



Rapport technique

2016

Open Access

This version of the publication is provided by the author(s) and made available in accordance with the copyright holder(s).

Size and mass distributions of particles and polymers

Borkovec, Michal

How to cite

BORKOVEC, Michal. Size and mass distributions of particles and polymers. 2016

This publication URL: <https://archive-ouverte.unige.ch/unige:148740>

Size and mass distributions of particles and polymers


Michal Borkovec

Email. michal.borkovec@unige.ch

November 22, 2016

Direct link www.colloid.ch/distributions

Truly *monodisperse* particles or polymers are rare. Examples of such systems, where all constituents are molecularly identical, are clusters of relatively small number of atoms (e.g., buckminsterfullerene) or proteins with a well-defined sequence of amino acids. Typically, however, colloidal particles, nanoparticles, polymers, or biomacromolecules are *polydisperse*, meaning that in a sample one finds a distribution of similar objects, which vary in size and mass, possibly in shape [1]. When the systems are composed of one type of material, they are often referred to as *homogeneous*, while systems containing different types of materials called *heterogeneous*. One may discuss size distributions in the latter systems as well. These notions are illustrated in the figure below.

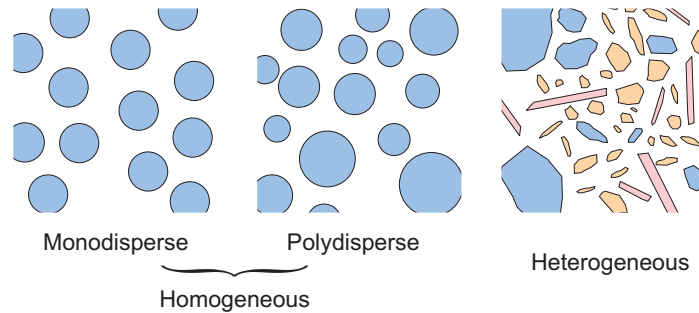

Size distributions can be relatively narrow, and in such situations one may neglect polydispersity effects to a first approximation. Various types of particles can be fabricated in close to spherical shape and with small degree of polydispersity (e.g., latex, silica, gold). Various types of polymers with low polydispersity can be synthesized as well (e.g., polystyrene) [2]. More frequently, however, size distributions have a finite width, and can be extremely wide, sometimes covering many orders of magnitude in size or mass. In such cases, various system properties are dominated by polydispersity effects. Such systems can be heterogeneous too. Naturally occurring particles or polymers often fall into that class (e.g., dust, soil, polysaccharides, humic substances) [3,4]. While this essay only focusses on size distributions of particles and polymers, similar notions can also be used to discuss size distributions of other objects, such as colloidal aggregates, stones, animals, stars, or galaxies.

Size and mass distributions

Consider homogeneous and spherical (or at least approximatively spheroidal) particles, which can be characterized by the radius R of an equivalent sphere. In a given size range, there is certain number of such particles per unit volume, namely $n(R)dR$ in the range of radii R and $R + dR$. The total number of particles per unit volume N , which is also referred to as the number concentration, is given by

$$N = \int_0^{\infty} n(R)dR$$

The corresponding *number weighted size distribution* can be thus expressed as

$$p(R) = \frac{n(R)}{N}$$

This function is a probability distribution as it is normalized to unity by virtue of the relation given further above. A similar probability distribution can also be introduced for non-spherical objects, whereby one defines its radius in terms of the radius of an equivalent sphere with the same volume. For strongly non-spherical objects (e.g., rods, platelets) one should rather consider multi-variate distributions of the different object dimensions (e.g., length, width, thickness). That scenario can be relevant, but will not be discussed here.

The (molar) mass of polymers is more easily measured than its size, and for this reason one rather refers to mass distributions. In analogy to the above definition, one discusses the number of such particles in a given mass range, namely $n'(M)dM$ in the range of masses between M and $M + dM$. As a consequence, one may introduce a *number weighted mass distribution* denoted by

$$q(M) = \frac{n'(M)}{N}$$

For spherical particles, their mass and radius are obviously related through the density of the particle. A similar relation also applies for other objects, and thus we consider

$$M = KR^d$$

For compact objects, $d = 3$ and the constant K depends on the density and shape. For polymers or colloidal aggregates, however, the exponent can assume non-integer values ($d < 3$). Such objects are referred to as mass fractals, and the exponent d as the *mass fractal dimension*. Few relevant values of these exponents are given in the table below. Particle aggregates are also mass fractals, and their fractal dimension depends whether one deals with rapid diffusion limited colloidal aggregation (DLCA) or slow reaction limited colloidal aggregation (RLCA) [5].

Object	d
Polymers in good solvent	1.7
DLCA particle aggregates	1.9
Polymers in θ -solvent	2.0
RLCA particle aggregates	2.1
Compact object	3.0

For such objects, an equivalent radius must be appropriately defined, for example, through its gyration radius. From the above relation, one finds that $q(M)dM = p(R)dR$ and thus that $q(M) \propto p(R)R/M$. The proportionality constant can be found by normalization.

When discussing size distributions, researchers often refer to the *mass weighted size distribution*. Thereby, one considers the mass of particles per unit volume $M(R)n(R)dR$ within a given interval R and $R + dR$. The resulting probability distribution reads

$$p_\alpha(R) = \frac{R^\alpha p(R)}{\int_0^\infty R^\alpha p(R) dR}$$

where $\alpha = 3$ must be used for compact objects. The special feature of particle size distributions is that one must also be able to normalize the mass weighted distribution, since the sample has a finite mass. This condition represents a constraint on possible choices of valid size distributions.

For $\alpha = 0$ the number weighted size distribution is recovered. Other weights can be used. For example, $\alpha = 2$ leads to the *area weighted size distribution* for compact and smooth objects. The *intensity weighted size distribution* is sometimes discussed in the interpretation of light scattering

data and for compact objects it is obtained by setting $\alpha = 6$. Cumulative size distributions are also frequently used, which are introduced as the undersize fraction

$$P_\alpha(R) = \int_0^R p_\alpha(R') dR'$$

or the oversize fraction

$$Q_\alpha(R) = 1 - P_\alpha(R) = \int_R^\infty p_\alpha(R') dR'$$

Again, different weights for these cumulative fractions can be used. Similarly, one may consider the *mass weighted mass distribution*, which is obtained from

$$q_\alpha(R) = \frac{M^\alpha q(M)}{\int_0^\infty M^\alpha q(M) dM}$$

by setting $\alpha = 1$. For $\alpha = 0$ one obtains the number weighted mass distribution. The condition of a finite mass translates into the requirement that the mass weighted mass distribution must be normalizable. The corresponding cumulative mass distributions are less frequently used, but they could be defined similarly.

Moments and averages

An important characteristics of any probability distribution are their moments. The moments of order α of the number weighted size distribution are defined by

$$\langle R^\alpha \rangle = \int_0^\infty R^\alpha p(R) dR$$

where $\langle \dots \rangle$ denotes the expectation value. Among these moments, the most important ones are of order one and two. The first moment corresponds to the average radius given by $\langle R \rangle$ and it characterizes the average particle size. The second moment is related to the relative width of the distribution through the normalized standard deviation ϵ_R , which is also referred to as the coefficient of variation or polydispersity, and is normally expressed as

$$\frac{\langle R^2 \rangle}{\langle R \rangle^2} = D_R = 1 + \epsilon_R^2$$

This equation also introduces the *size polydispersity index* D_R . We already mentioned the characteristic feature of particle size distributions, namely that its mass weighted distribution must be normalizable. This condition is equivalent to the condition that the moment $\langle R^d \rangle$ is finite.

Similar moments can be defined for the mass distribution. The average mass $\langle M \rangle$ is also referred to as the *number weighted average mass* denoted as M_n . The condition that mass weighted mass distribution is normalizable implies that the first moment $\langle M \rangle$ must be finite. The polydispersity can be again expressed in terms of the normalized standard deviation ϵ_M or the *mass polydispersity index* D_M as

$$\frac{\langle M^2 \rangle}{\langle M \rangle^2} = D_M = 1 + \epsilon_M^2$$

In polymer literature, one commonly uses the polydispersity (or dispersity) mass index D_M , while normalized mass standard deviation ϵ_M is rarely used. This situation is contrary to the particle literature, where one rather uses the normalized size standard deviation ϵ_R , while the respective polydispersity size index D_R is not considered. Here we will rather use the relevant normalized standard deviations.

Clearly, the moments over the mass distribution are related to the ones over the size distribution, namely

$$\langle M^\alpha \rangle = K \langle R^{\alpha d} \rangle$$

In particular, the number weighted average mass becomes

$$M_n = M_n^{(0)} \frac{\langle R^d \rangle}{\langle R \rangle^d} = M_n^{(0)} \left[1 + \frac{d(d-1)}{2} \epsilon_R^2 + \dots \right]$$

where $M_n^{(0)}$ refers to a monodisperse sample containing only particles or polymers of radius $\langle R \rangle$. The mass polydispersity index becomes

$$D_M = \frac{\langle R^{2d} \rangle}{\langle R^d \rangle^2} = 1 + d^2 \epsilon_R^2 + \dots$$

The second equation signs are valid for any size distribution with sufficiently small polydispersity and can be obtained by expanding the arguments in a Taylor series around $\langle R \rangle$. Indeed, the mass polydispersity is larger than the one by size, and for not too polydisperse samples, one has $\epsilon_M = d\epsilon_R$.

Model distributions

A normal (or Gaussian) distribution is unsuitable to model size or mass distributions. The reason is that this distribution always yields a finite probability for negative arguments, which is incompatible with the fact that the particle radii or masses are always positive. However, this problem can be remedied by assuming that the logarithm of the radius follows a normal distribution, which leads to the log-normal distribution [6]

$$p(R) \propto R^{-1} e^{-(\ln R - \mu)^2 / (2v)}$$

where $v = \ln(1 + \epsilon_R^2)$ and $\mu = \ln \langle R \rangle - v/2$. The advantage of this distribution is that its moments can be simply expressed as

$$\langle R^\alpha \rangle = \langle R \rangle^\alpha (1 + \epsilon_R^2)^{\alpha(\alpha-1)/2}$$

where α is the (possibly fractional) order of the moment. Another suitable size distribution is the exponential (or Schultz) distribution [7]

$$p(R) \propto R^{\nu-1} e^{-\beta R}$$

where $\beta = \nu / \langle R \rangle$ and $\nu = 1/\epsilon_R^2 > 0$. All its moments can be again evaluated analytically, namely


$$\langle R^\alpha \rangle = \langle R \rangle^\alpha \cdot \frac{\Gamma(\nu + \alpha)}{\nu^\alpha \Gamma(\nu)}$$

where $\Gamma(x)$ is Euler's gamma function. Note that the log-normal and exponential distributions can be approximated by a normal distribution for sufficiently small polydispersities.

Such distributions are illustrated in the figure on the next page. The left panel shows the exponential distribution for an average radius of 10 nm and different size polydispersities. The other panels show the resulting mass distributions for two different situations. The middle panel shows the resulting mass distribution for spherical and compact silica particles with $M_n^{(0)} = 6567$ kg/mol ($d = 3$). The left panel shows the analogous situation for polystyrene in tetrahydrofuran, which is a good solvent with $M_n^{(0)} = 100$ kg/mol ($d = 1.7$) [8]. For the polymer, the radius is defined as the gyration radius. One observes that the mass polydispersities are larger, especially for the compact particles.

Another relevant size distribution is the power law. This kind of distribution is commonly written as [3,4]

$$p(R) \propto R^{-\delta-1}$$

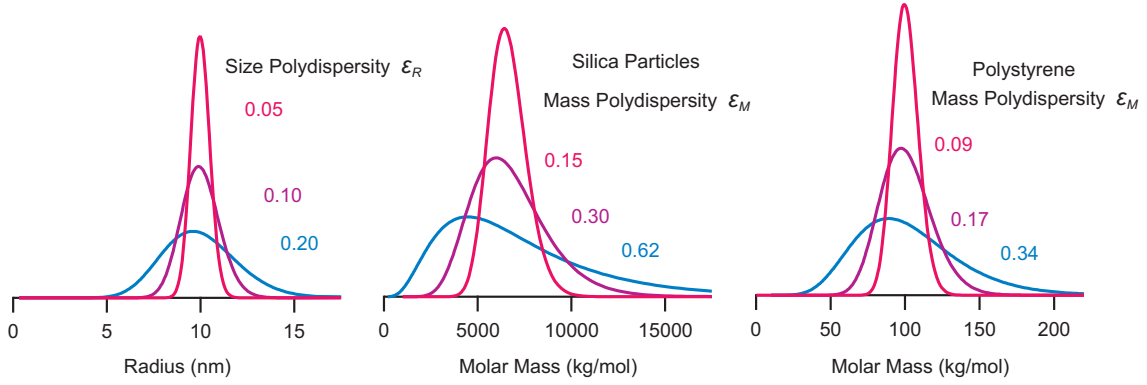

where δ is referred to as the *fragmentation fractal dimension*. In this situation, this distribution cannot be easily normalized, and the particle mass may also diverge. To avoid these problems, one assumes that this distribution is only valid in a finite range of radii between R_{\min} and R_{\max} . In this case, the moments can be again calculated explicitly. In practical situations, these cut-off radii may differ by many orders of magnitude. These cut-offs can be also achieved by smooth functions, for example, by exponential functions or power-laws with different exponents [4].

The undersize and oversize fractions shown on the next page illustrate the special features of the power distribution. The fragmentation fractal dimension is taken to be $\delta = 2.7$ as is often the case for size distributions of naturally occurring particles [4]. The cutoff radii are chosen to be $R_{\min} = 1$ nm and $R_{\max} = 1000$ nm. One observes that the largest contribution to the particle number occurs at R_{\min} while the one to the particle mass at R_{\max} . Therefore, entirely different parts of the size distribution dominate these characteristics.

Once the size distribution is known, the mass distribution $q(M)$ can be easily evaluated. For the log-normal and power distribution, the mass distributions are again log-normal and power distributions. Only the respective parameters of the distribution must be modified accordingly. For the power distribution, in particular, only the exponent is modified as $q(M) \propto M^{-\delta/d-1}$. In the case of the Schultz distribution, the mass distribution assumes a different functional form, namely the generalized exponential distribution. However, the exponential distribution can also be used to model the mass distribution $q(M)$. In that case, one must define the underlying parameters accordingly.

Characterization techniques


Various experimental techniques can be used to measure the particle size or the (molar) mass. In the following, the effect of polydispersity on the results from these techniques will be summarized. On the other hand, no detailed treatment of these techniques will be given, and the reader is referred to literature [2].

Osmotic pressure measurements extrapolated to low concentrations are often used to measure the molar mass. The osmotic pressure is proportional to the number concentration, but only the mass concentration of the particles or polymers is known. The latter is related to the number weighted (molar) mass, $\langle M \rangle$ or M_n , and therefore this quantity can be extracted from this experiment.

Static light scattering and ultracentrifugation allow the measurement of the mass weighted (molar) mass or the weight averaged molar mass

$$M_w = \frac{\langle M^2 \rangle}{\langle M \rangle} = M_w^{(0)} \frac{\langle R^{2d} \rangle}{\langle R^d \rangle \langle R \rangle^d} = M_w^{(0)} \left[1 + \frac{d(3d-1)}{2} \epsilon_R^2 + \dots \right]$$

where $M_w^{(0)}$ refers to a monodisperse sample containing only particles or polymers of radius $\langle R \rangle$.

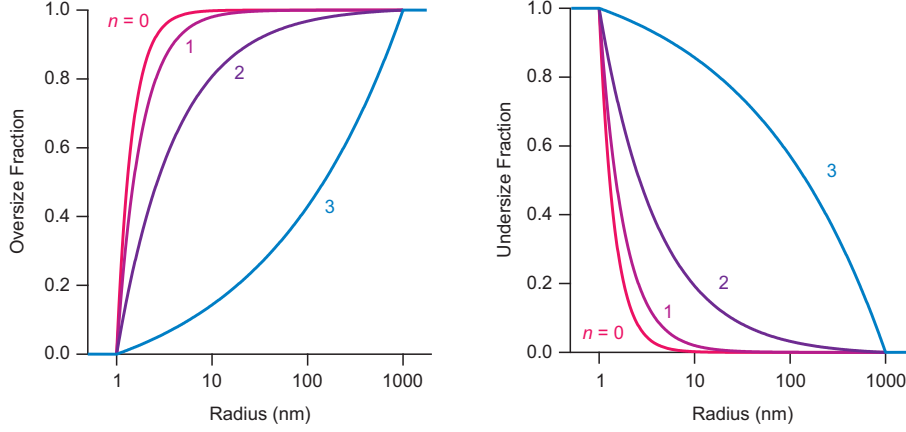

Given this definition the mass polydispersity index can also be expressed as $D_M = M_w/M_n$. In static light scattering, the (molar) mass is obtained from the scattering intensity extrapolated to low concentrations and small scattering angles. In ultracentrifugation, one measures the equilibrium sedimentation profile by light absorption, and from the dependence of the concentration profile from the distance from the rotation axis, the (molar) mass can be extracted. Note that the average $\langle M^3 \rangle / \langle M^2 \rangle$ can also be relevant in ultracentrifugation, provided the concentration measurement was carried out through the refractive index. However, this measurement technique is hardly used today anymore.

Static light scattering can be also used to measure the gyration radius, which is obtained from the dependence of the scattering intensity on the scattering angle at small angles. The respective average for a polydisperse sample is given by

$$R_g = R_g^{(0)} \left(\frac{\langle R^{2d+2} \rangle}{\langle R^{2d} \rangle \langle R^2 \rangle} \right)^{1/2} = R_g^{(0)} \left(1 + \frac{4d+1}{2} \epsilon_R^2 + \dots \right)$$

where $R_g^{(0)}$ is the gyration radius of the respective monodisperse sample. With dynamic light scattering, one measures the diffusion coefficient, which can be expressed in terms of the hydrodynamic radius by means of the Stokes-Einstein relation. In this case, the relevant moments for a polydisperse sample are

$$R_h = R_h^{(0)} \frac{\langle R^{2d} \rangle}{\langle R \rangle \langle R^{2d-1} \rangle} = R_h^{(0)} [1 + (2d-1) \epsilon_R^2 + \dots]$$

where $R_h^{(0)}$ is the hydrodynamic radius of the monodisperse sample.


Measurements of the viscosity of the polymer solution is another popular way to obtain the molecular mass of polymers. Thereby, one investigates the Staudinger index (or the intrinsic viscosity) $[\eta]$ for different molecular masses, which obeys the power-law relationship [2]

$$[\eta] = A M_\eta^\gamma$$

where M_η is the *viscosity averaged (molar) mass* and A is a constant. The exponent γ is actually related to the mass fractal dimension of the polymer through $\gamma = 3/d - 1$. The respective average of the molar mass is given by

$$M_\eta = \left(\frac{\langle M^{\gamma+1} \rangle}{\langle M \rangle} \right)^{1/\gamma} = M_\eta^{(0)} \left(\frac{\langle R^3 \rangle^d}{\langle R^d \rangle^3} \right)^{1/(3-d)} = M_\eta^{(0)} \left(1 + \frac{3d}{2} \epsilon_R^2 + \dots \right)$$

where $M_\eta^{(0)}$ refers to a monodisperse sample containing only particles or polymers of radius $\langle R \rangle$. Note that the molar mass cannot be determined by means of the viscosity method for compact objects ($d = 3$). However, this limit is well behaved for the averages above.

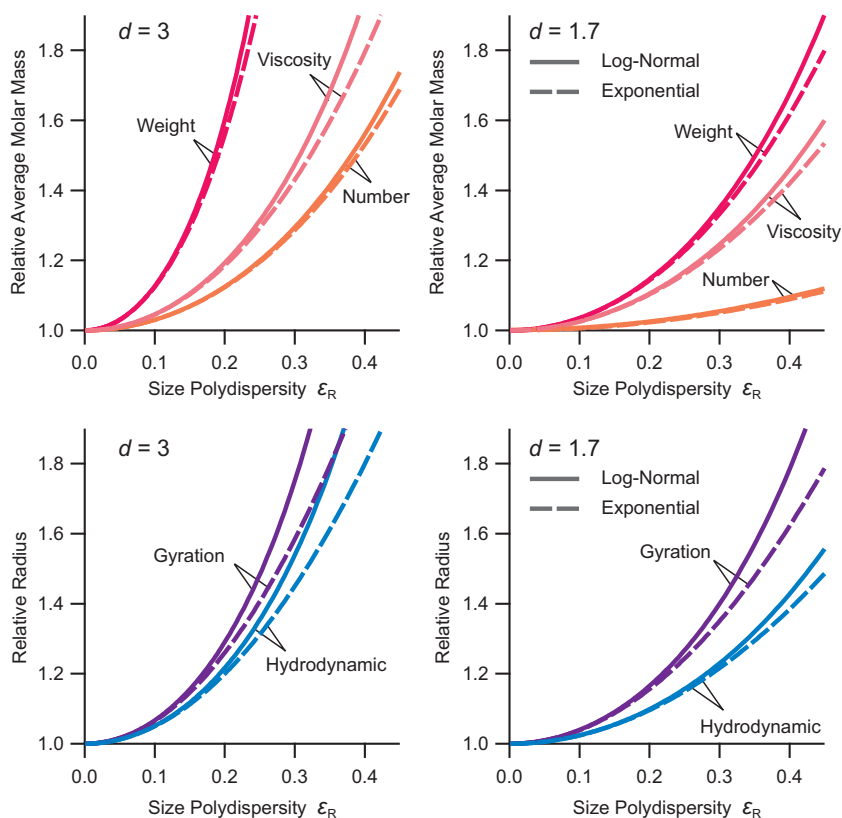

Conclusion

The present text serves as a summary of different notions surrounding size and mass distributions used in literature. While several concepts discussed are often used in different fields individually, they are all interconnected, and these connections are not always well documented. Particularly, the relations between the size and mass distributions are worked out here. The present developments may be helpful to achieve a more unified view of size or mass distributions.

First posted, November 22, 2016. Last revision, November 22, 2016.

This work is licensed under a Creative Commons Attribution 4.0 International License.

References

- [1] Allen T. (1975) Particle size measurement, Chapman and Hall.
- [2] Elias H. G. (1997) Introduction to Polymer Science, VCH Publishers.
- [3] Friedlander S. K. (2000) Smoke, Dust, and Haze, 2nd edition, Oxford University Press.
- [4] Wu Q., Borkovec M., Sticher H. (1993) On particle size distributions in soils, Soil Sci. Soc. Am. J. 57, 883-890.
- [5] Sandkuhler P., Lattuada M., Wu H., Sefcik J., Morbidelli M. (2005) Further insights into the universality of colloidal aggregation, Adv. Colloid Interface Sci. 113, 65-83.
- [6] Wikipedia, Log-normal distribution, https://en.wikipedia.org/wiki/Log-normal_distribution
- [7] Wikipedia, Exponential distribution, https://en.wikipedia.org/wiki/Exponential_distribution
- [8] M. Bhatt, A. M. Jamieson (1989) Configurational dynamics of high molecular weight polystyrenes in good solvents, Macromolecules, 22, 2724-2730.