



Article scientifique

Article

2015

Published version

Open Access

This is the published version of the publication, made available in accordance with the publisher's policy.

---

All-ceramic or metal-ceramic tooth-supported fixed dental prostheses (FDPs)? A systematic review of the survival and complication rates. Part II: Multiple-unit FDPs

---

Pjetursson, Bjarni Elvar; Sailer, Irena; Makarov, Nikolay Alexandrovich; Zwahlen, Marcel; Thoma, Daniel Stefan

#### How to cite

PJETURSSON, Bjarni Elvar et al. All-ceramic or metal-ceramic tooth-supported fixed dental prostheses (FDPs)? A systematic review of the survival and complication rates. Part II: Multiple-unit FDPs. In: Dental materials, 2015, vol. 31, n° 6, p. 624–639. doi: 10.1016/j.dental.2015.02.013

This publication URL: <https://archive-ouverte.unige.ch/unige:79012>

Publication DOI: [10.1016/j.dental.2015.02.013](https://doi.org/10.1016/j.dental.2015.02.013)

Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

ScienceDirect

journal homepage: [www.intl.elsevierhealth.com/journals/dema](http://www.intl.elsevierhealth.com/journals/dema)

## Review

# All-ceramic or metal-ceramic tooth-supported fixed dental prostheses (FDPs)? A systematic review of the survival and complication rates. Part II: Multiple-unit FDPs<sup>☆</sup>



Bjarni Elvar Pjetursson<sup>a,\*</sup>, Irena Sailer<sup>b</sup>, Nikolay Alexandrovich Makarov<sup>b</sup>, Marcel Zwahlen<sup>c</sup>, Daniel Stefan Thoma<sup>d</sup>

<sup>a</sup> Division of Reconstructive Dentistry, Faculty of Odontology, University of Iceland, Reykjavík, Iceland

<sup>b</sup> Division of Fixed Prosthodontics and Biomaterials, Clinic of Dental Medicine, University of Geneva, Switzerland

<sup>c</sup> Institute of Social and Preventive Medicine, University of Berne, Berne, Switzerland

<sup>d</sup> Clinic of Fixed and Removable Prosthodontics and Dental Material Science, University of Zurich, Zurich, Switzerland

## ARTICLE INFO

## Article history:

Received 7 July 2014

Received in revised form

24 February 2015

Accepted 27 February 2015

## Keywords:

All-ceramic

Metal-ceramic

Fixed partial dentures

Systematic review

Survival

Success

Longitudinal

Failures

Technical complications

Biological complications

## ABSTRACT

**Objective.** To assess the 5-year survival of metal-ceramic and all-ceramic tooth-supported fixed dental prostheses (FDPs) and to describe the incidence of biological, technical and esthetic complications.

**Methods.** Medline (PubMed), Embase and Cochrane Central Register of Controlled Trials (CENTRAL) searches (2006–2013) were performed for clinical studies focusing on tooth-supported FDPs with a mean follow-up of at least 3 years. This was complemented by an additional hand search and the inclusion of 10 studies from a previous systematic review [1]. Survival and complication rates were analyzed using robust Poisson's regression models to obtain summary estimates of 5-year proportions.

**Results.** Forty studies reporting on 1796 metal-ceramic and 1110 all-ceramic FDPs fulfilled the inclusion criteria. Meta-analysis of the included studies indicated an estimated 5-year survival rate of metal-ceramic FDPs of 94.4% (95% CI: 91.2–96.5%). The estimated survival rate of reinforced glass ceramic FDPs was 89.1% (95% CI: 80.4–94.0%), the survival rate of glass-infiltrated alumina FDPs was 86.2% (95% CI: 69.3–94.2%) and the survival rate of densely sintered zirconia FDPs was 90.4% (95% CI: 84.8–94.0%) in 5 years of function. Even though the survival rate of all-ceramic FDPs was lower than for metal-ceramic FDPs, the differences did not reach statistical significance except for the glass-infiltrated alumina FDPs ( $p = 0.05$ ). A significantly higher incidence of caries in abutment teeth was observed for densely sintered zirconia FDPs compared to metal-ceramic FDPs. Significantly more framework fractures were reported for reinforced glass ceramic FDPs (8.0%) and glass-infiltrated alumina FDPs

<sup>☆</sup> This paper was originally intended for publication with the set of papers from the Academy of Dental Materials Annual Meeting, 8–11 October 2014, Bologna, Italy; published in DENTAL 31/1 (2015).

\* Corresponding author at: Department of Reconstructive Dentistry, Faculty of Odontology, University of Iceland, Vatnsmyrarvegi 16, 101 Reykjavík, Iceland. Tel.: +354 525 4871.

E-mail address: [bep@hi.is](mailto:bep@hi.is) (B.E. Pjetursson).

<http://dx.doi.org/10.1016/j.dental.2015.02.013>

0109-5641/© 2015 Academy of Dental Materials. Published by Elsevier Ltd. All rights reserved.

(12.9%) compared to metal-ceramic FDPs (0.6%) and densely sintered zirconia FDPs (1.9%) in 5 years in function. However, the incidence of ceramic fractures and loss of retention was significantly ( $p = 0.018$  and  $0.028$  respectively) higher for densely sintered zirconia FDPs compared to all other types of FDPs.

**Conclusions.** Survival rates of all types of all-ceramic FDPs were lower than those reported for metal-ceramic FDPs. The incidence of framework fractures was significantly higher for reinforced glass ceramic FDPs and infiltrated glass ceramic FDPs, and the incidence for ceramic fractures and loss of retention was significantly higher for densely sintered zirconia FDPs compared to metal-ceramic FDPs.

© 2015 Academy of Dental Materials. Published by Elsevier Ltd. All rights reserved.

## Contents

|                                                                                               |     |
|-----------------------------------------------------------------------------------------------|-----|
| 1. Introduction .....                                                                         | 625 |
| 2. Materials and methods .....                                                                | 627 |
| 2.1. Search strategy .....                                                                    | 627 |
| 2.2. Focused questions .....                                                                  | 627 |
| 2.3. PICO .....                                                                               | 627 |
| 2.4. Search terms .....                                                                       | 627 |
| 2.5. Inclusion criteria .....                                                                 | 627 |
| 2.6. Exclusion criteria .....                                                                 | 627 |
| 2.7. Selection of studies .....                                                               | 627 |
| 2.8. Data extraction and method of analysis .....                                             | 627 |
| 2.9. Statistical analysis .....                                                               | 629 |
| 3. Results .....                                                                              | 629 |
| 3.1. Study characteristics .....                                                              | 629 |
| 3.2. FDP survival .....                                                                       | 630 |
| 3.3. Biological complications .....                                                           | 633 |
| 3.3.1. Secondary caries .....                                                                 | 633 |
| 3.3.2. Loss of vitality .....                                                                 | 635 |
| 3.3.3. Abutment tooth fracture .....                                                          | 635 |
| 3.3.4. Periodontal disease .....                                                              | 635 |
| 3.4. Technical complications .....                                                            | 635 |
| 3.4.1. Material complications: framework fracture, ceramic chipping or ceramic fracture ..... | 635 |
| 3.4.2. Loss of retention .....                                                                | 636 |
| 3.4.3. Marginal discoloration .....                                                           | 636 |
| 4. Discussion .....                                                                           | 636 |
| 5. Conclusion .....                                                                           | 638 |
| Conflict of interest .....                                                                    | 638 |
| Acknowledgments .....                                                                         | 638 |
| Excluded studies and reasons for exclusion .....                                              | 638 |
| References .....                                                                              | 638 |

## 1. Introduction

Socio-economic factors, better prophylaxis and oral hygiene regimens with patients included in regular recall programs have led to an increased number of teeth and to a shift from fully to more partially edentulous patients over the past decades [2]. This resulted in more single and multiple tooth gaps that can be restored with fixed tooth- or implant-supported reconstructions. In order to support the decision-making process for either one option, evidence-based clinical data are needed reporting on survival and

complication rates for both types of reconstructions. Whereas for implant-supported reconstructions, systematic reviews provide very recent evidence comparing metal- and all-ceramic reconstructions [3,4], a systematic pooling of newer clinical data on tooth-supported reconstructions is limited to all-ceramic reconstructions [5].

Traditionally, metal-based reconstructions for fixed dental prostheses (FDPs) were considered as the gold standard [6]. Alloys, mainly gold-based, were fully or partially veneered with feldspathic ceramics. The evolution in material science led to the introduction of new framework materials

(ceramics) and partially a change in clinical concepts (e.g. monolithic rather than veneered framework materials) [7–10]. Ceramics as part of reconstructive materials fulfill the need for esthetics. However, low-strength materials such as feldspathic-based ceramics and (reinforced) glass-ceramic materials appear to be more suitable for single crowns than for FDPs [7,11]. In order to overcome the limited material properties, high-strength ceramics were introduced in dentistry. Zirconia as the most stable of these materials is available for CAD/CAM technology and offers a higher flexural strength (900–1400 MPa) and a higher fracture toughness ( $5\text{--}10\text{ MPa m}^{1/2}$ ) [12,13]. Zirconia is mainly used as a framework material for single crowns and FDPs [14–16]. Zirconia used as framework material appears to withstand the clinical forces during chewing and regular function and fracture rates are low and comparable to metal-based FDPs [17]. However, in contrast to metal-based FDPs, a higher rate of technical complications (major chippings) was reported [18,19]. The adhesion between zirconia and veneering ceramics is reported to be the critical issue for this observation [20].

In a systematic review, analyzing the survival and complications rates of all-ceramic and metal-ceramic reconstructions, an imbalance in terms of the number of studies for all-ceramic and metal-based FDPs was observed [1]. Clinical studies on newer materials such as zirconia, lithium disilicate reinforced glass ceramics and glass-infiltrated alumina (In-Ceram Alumina) or glass-infiltrated alumina-zirconia (Inceram-Zirconia) were available, but only few of them provided longer term data. Since that time, the evidence increased and clinical data are available for a number of all-ceramic materials for FDPs. The aim of the present systematic review was therefore,

- (i) to update the previous systematic review [1] on tooth-supported FDPs with an additional literature search including retrospective and prospective studies from 2007 to 2013;
- (ii) to assess the 3-year survival rate of tooth-supported fixed dental prostheses (FDPs) and to describe the rate of biological, technical and esthetic complications;

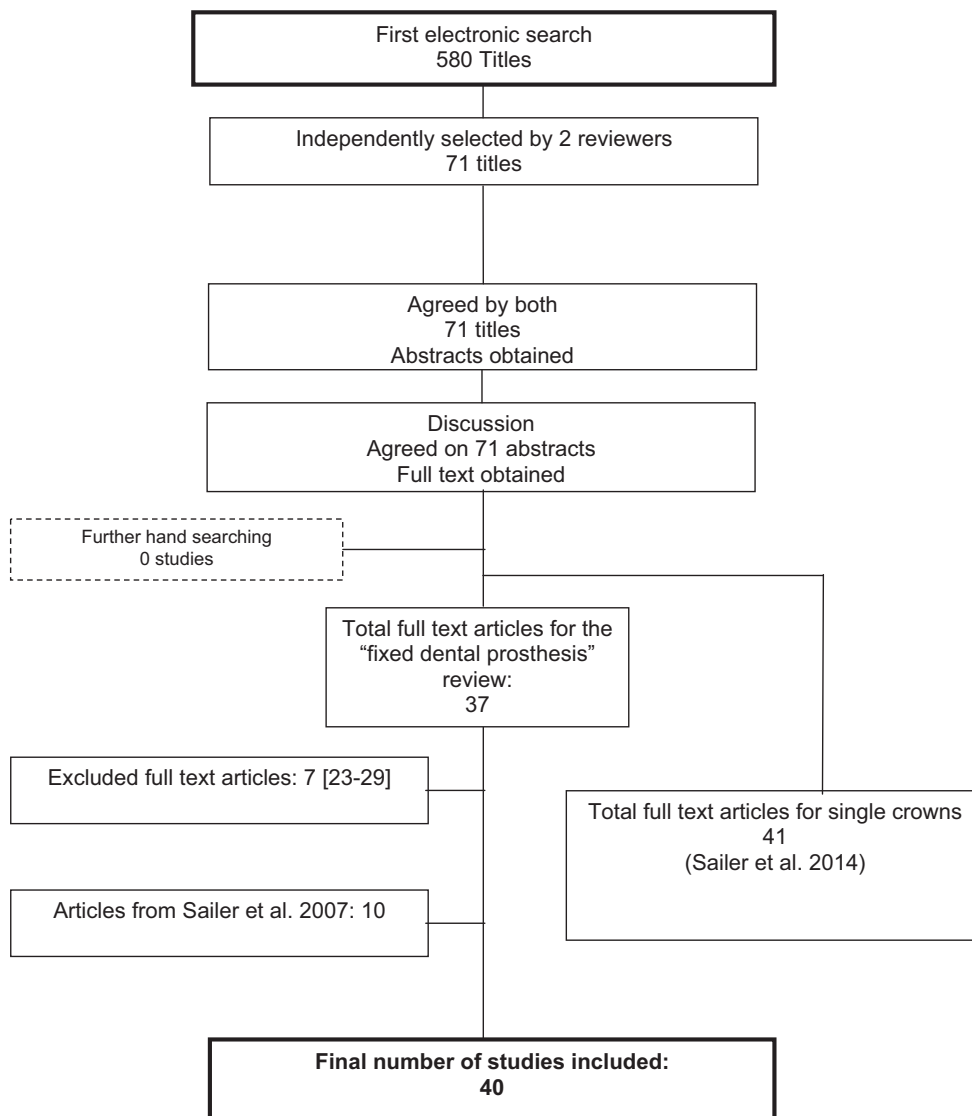


Fig. 1 – Search strategy.

- (iii) to compare the survival and complication rates of metal-based FDPs and all-ceramic FDPs.

## 2. Materials and methods

### 2.1. Search strategy

This systematic review was designed as an update to a previously prepared publication with the same objectives [1]. For that purpose, Medline (PubMed), Embase and Cochrane Central Register of Controlled Trials (CENTRAL) searches were performed for clinical studies, including articles published from December 1st, 2006 up to December 31, 2013 in the Dental literature. The search was limited to the English language (Fig. 1).

### 2.2. Focused questions

“What are the survival and complication rates of tooth-supported FDPs after a mean observation period of at least 3 years?” “Are the survival and complications rates of metal-ceramic and all-ceramic tooth-supported FDPs similar after a mean observation period of at least 3 years?”

### 2.3. PICO

The PICO for the present systematic review was defined as follows:

- P Population: subjects with anterior and/or posterior fixed tooth-supported FDPs
- I Intervention: all-ceramic FDP
- C Comparison: metal-ceramic FDP
- O Outcome: clinical survival and technical, biological and esthetic complication rates

### 2.4. Search terms

The following four searches and search terms were applied:

Population and intervention  
crowns[MeSH] OR crown[MeSH] OR dental crowns[MeSH] OR crowns, dental[MeSH] OR Denture, Partial, Fixed[Mesh]) OR (crown\*[all fields] OR fixed partial denture\*[all fields] OR FPD[all fields] OR FPDs[all fields] OR fixed dental prosthesis[all fields] OR fixed dental prostheses[all fields] OR FDP[all fields] OR FDPs[all fields] OR bridge\*[all fields]

comparison  
ceramic[MeSH] OR ceramics[MeSH] OR metal ceramic restorations[MeSH]) OR (ceramic\*[All Fields] OR all-ceramic[all fields] OR Dental Porcelain[All Fields] OR metal-ceramic[All Fields]

outcome  
Survival[Mesh] OR survival rate[Mesh] OR survival analysis[Mesh] OR dental restoration failure[Mesh] OR prosthesis failure[Mesh] OR treatment failure[Mesh].

The search combination in the builder was “population AND intervention AND comparison AND outcome”.

An additional hand search was performed identifying relevant studies by screening the reference list of all included publications.

### 2.5. Inclusion criteria

Clinical publications were considered if all of the following criteria were suitable: (i) human trials with a minimum amount of 10 patients with FDPs, (ii) mean follow-up of at least 3 years in function, (iii) randomized controlled trials (RCT), controlled clinical trials (CCT), prospective case series, cohort studies, retrospective studies, (iv) patients needed to be examined clinically, and (v) reported details of materials characteristics, methods and results.

### 2.6. Exclusion criteria

Studies not meeting all inclusion criteria were excluded from the review. Publications dealing with the following topics were also excluded: in vitro and preclinical studies, studies with a follow-up of less than 3 years, reports based on questionnaires, interviews and charts.

### 2.7. Selection of studies

Two authors (IS, NAM) independently screened the titles derived from the searches based on the inclusion criteria. Disagreements were resolved by discussion. Following this, abstracts of all titles agreed on by both authors were obtained, and screened for meeting the inclusion criteria. If no abstract was available in the database, the abstract of the printed article was used. Based on the selection of abstracts, articles were then obtained in full text. If title and abstract did not provide sufficient information regarding the inclusion criteria, the full report was obtained as well. Again, disagreements were resolved by discussion.

The final selection based on inclusion/exclusion criteria was made for the full text articles. For this purpose Materials and Methods, Results and Discussion of these studies were screened. This step was again carried out by 2 readers (IS, NAM) and double-checked. Any questions that came up during the screening were discussed to aim for consensus. In addition, 15 publications from the previous systematic review [1] were included in the analyses.

### 2.8. Data extraction and method of analysis

All included articles were independently screened and data extracted using data extraction tables by two reviewers (DTH, BPJ). Any disagreements were resolved by discussion to aim for consensus. In addition, data of the included publications of the previously published review [1] were extracted as well.

Data on the following parameters were extracted: author(s), year of publication, study design, planned number of patients, actual number of patients at end of study, drop-out rate, mean age, age range, operators, material framework, brand name of framework material, veneering material, brand name of veneering material, type of manufacturing procedure, number of FDPs, number of abutment teeth, number of (non)vital abutment teeth, number of pontics, location of FDP

**Table 1 – Study and patient characteristics of the reviewed studies for all-ceramic FPDs.**

| Study                   | Year of publication | Framework material                          | Study design | No. of patients in study | Age range | Mean age | Setting                          | Drop-out (in percent) |
|-------------------------|---------------------|---------------------------------------------|--------------|--------------------------|-----------|----------|----------------------------------|-----------------------|
| Sola-Ruiz et al.        | 2013                | Lithium disilicate reinforced glass ceramic | Prosp.       | 19                       | n.r.      | 49       | University                       | 0%                    |
| Rinke et al.            | 2013                | Zirconia                                    | Prosp.       | 75                       | 26–76     | 49.4     | University                       | 19%                   |
| Raigrodski et al.       | 2012                | Zirconia                                    | Prosp.       | 16                       | 36–60     | 48       | University                       | 6%                    |
| Peleaz et al.           | 2012                | Zirconia                                    | RCT          | 37                       | 23–65     | n.r.     | University                       | 0%                    |
| Sagitkaya et al.        | 2012                | Zirconia                                    | Prosp.       | 28                       | n.r.      | 38       | University                       | 0%                    |
| Kern et al.             | 2012                | Lithium disilicate reinforced glass ceramic | Prosp.       | 28                       | n.r.      | 47.5     | University                       | 7%                    |
| Lops et al.             | 2012                | Zirconia                                    | Prosp.       | 28                       | n.r.      | 46.2     | University                       | 14%                   |
| Sax et al.              | 2011                | Zirconia                                    | Prosp.       | 45                       | n.r.      | 48.3     | University                       | 53%                   |
| Sorrentino et al.       | 2011                | Zirconia                                    | Prosp.       | 37                       | 21–68     | 45.3     | University                       | 0%                    |
| Makarouna et al.        | 2011                | Lithium disilicate reinforced glass ceramic | RCT          | 19                       | n.r.      | 47       | University                       | 26%                   |
| Schmitt et al.          | 2011                | Zirconia                                    | Prosp.       | 15                       | 29–73     | 50.1     | University                       | 0%                    |
| Christensen and Ploeger | 2010                | Zirconia and glass-infiltrated alumina      | RCT          | 259                      | 16–89     | 50       | Private practice multi-center    | 4%                    |
| Beuer et al.            | 2010                | Zirconia                                    | Prosp.       | 38                       | 27–71     | 50.9     | University                       | 0%                    |
| Roediger et al.         | 2010                | Zirconia                                    | Prosp.       | 75                       | 26–76     | 49.4     | University                       | 11%                   |
| Wolfart et al.          | 2009                | Lithium disilicate reinforced glass ceramic | Prosp.       | 29                       | 25–68     | 47.9     | Multi-Center                     | 7%                    |
| Eschbach et al.         | 2009                | Glass-infiltrated alumina-zirconia          | Prosp.       | 58                       | n.r.      | 46.8     | University                       | 3%                    |
| Sailer et al.           | 2009                | Zirconia                                    | RCT          | 59                       | n.r.      | 54.4     | University                       | 5%                    |
| Wolfart et al.          | 2009                | Zirconia                                    | Prosp.       | 48                       | 23–75     | 55       | University                       | 4%                    |
| Beuer et al.            | 2009                | Zirconia                                    | Prosp.       | 19                       | 27–71     | 50.9     | University                       | 0%                    |
| Edelhoff et al.         | 2008                | Zirconia                                    | Prosp.       | 18                       | n.r.      | n.r.     | University                       | 6%                    |
| Molin and Karlsson      | 2008                | Zirconia                                    | Prosp.       | 18                       | 40–84     | 59       | Specialists and private practice | 0%                    |
| Tinschert et al.        | 2008                | Zirconia                                    | Prosp.       | 46                       | 20–58     | n.r.     | University                       | 13%                   |
| Esquivel et al.         | 2008                | Lithium disilicate reinforced glass ceramic | Prosp.       | 21                       | 30–62     | n.r.     | University                       | 0%                    |
| Wolfart et al.          | 2005                | Lithium disilicate reinforced glass ceramic | Prosp.       | 29                       | 25–68     | 47.8     | University                       | 17%                   |
| Marquart and Strub      | 2005                | Lithium disilicate reinforced glass ceramic | Prosp.       | 43                       | 22–65     | 39.9     | University                       | 0%                    |
| Suàrez et al.           | 2004                | Glass-infiltrated alumina-zirconia          | Prosp.       | 16                       | 23–50     | n.r.     | University                       | 0%                    |
| Olsson et al.           | 2003                | Glass-infiltrated alumina                   | Retrospect.  | 37                       | 28–84     | 54       | Private practice                 | 16%                   |
| Vult von Steyern et al. | 2001                | Glass-infiltrated alumina                   | Prosp.       | 18                       | 25–70     | n.r.     | University and private practice  | 0%                    |
| Sorensen et al.         | 1998                | Glass-infiltrated alumina                   | Prosp.       | 47                       | 19–66     | n.r.     | University                       | 2%                    |

n.r., “not reported”; RCT, randomized controlled clinical trial.

(anterior, posterior, maxilla, mandible), reported mean follow-up, follow-up range, published FDP survival rate, number of FDPs lost (anterior, posterior), reported biological complications (caries, periodontal, root fracture), reported technical complications (framework fracture, minor chipping, major chipping, loss of retention), esthetic complications (marginal discoloration), reported number of patients free of complications. Based on the included studies, the FDP survival rate was calculated. In addition, the number of events for all technical, biological and esthetic complications was extracted and the corresponding total exposure time of the reconstruction was calculated.

## 2.9. Statistical analysis

Failure and complication rates were calculated by dividing the number of events (failures or complications) in the numerator by the total FDP exposure time in the denominator.

The numerator could usually be extracted directly from the publication. The total exposure time was calculated by taking the sum of:

- (1) Exposure time of FDPs that could be followed for the whole observation time.
- (2) Exposure time up to a failure of the FDPs that were lost due to failure during the observation time.
- (3) Exposure time up to the end of observation time for FDPs that did not complete the observation period due to reasons such as death, change of address, refusal to participate, non-response, chronic illnesses, missed appointments and work commitments.

For each study, event rates for the FDPs were calculated by dividing the total number of events by the total FDP exposure time in years. For further analysis, the total number of events was considered to be Poisson distributed for a given sum of FDP exposure years and Poisson regression with a logarithmic link-function and total exposure time per study as an offset variable were used [21].

Robust standard errors were calculated to obtain 95% confidence intervals of the summary estimates of the event rates. To assess heterogeneity of the study specific event rates, the Spearman goodness-of-fit statistics and associated *p*-value were calculated. If the goodness-of-fit *p*-value was below 0.05. Five-year survival proportions were calculated via the relationship between event rate and survival function  $S$ ,  $S(T) = \exp(-T \times \text{event rate})$ , by assuming constant event rates [22]. The 95% confidence intervals for the survival proportions were calculated by using the 95% confidence limits of the event rates. Multivariable Poisson regression was used to formally compare construction subtypes and to assess other study characteristics. All analyses were performed using Stata®, version 13.1.

### 3. Results

### 3.1. Study characteristics

A total of 40 studies fulfilled the inclusion criteria of the present systematic review. Seven studies were excluded for

**Table 2 – Study and patient characteristics of the reviewed studies for metal-ceramic FPDs.**

[illegible]



various reasons, ranging from multiple publications on the same patient cohort to insufficiently reported data on FDPs [23–29]. 28 studies, published between 1998 and 2013, on all-ceramic FDPs and 15 studies, published between 1989 and 2013, on metal ceramic FDPs, were included in this review (Tables 1 and 2). The median year of publications for all-ceramic FDPs was 2009 and for metal-ceramic FDPs 2010. For all-ceramic FDPs, the majority or 28 studies had a prospective design and only one had a retrospective design. In contrast, for metal-ceramic FDPs the majority of the included studies or 10 were retrospective and the remaining 5 studies were prospective. Four of the included studies (Peleaz et al., 2012, Makarouna, 2011, Christensen, 2010 and Sailer et al., 2009) were randomized controlled clinical trials comparing different types of all-ceramic FDPs with metal-ceramic FDPs. The included studies on all-ceramic FDPs reported on reconstructions made out of reinforced glass ceramics, glass-infiltrated alumina (InCeram Alumina), glass-infiltrated alumina-zirconia (InCeram Zirconia), and densely sintered zirconia (Table 1). The studies of metal-ceramic FDPs reported on reconstructions having framework out of gold metal, cobalt chromium or titanium (Table 2).

The majority of the included studies, or 35 out of 40 were conducted in university settings. The remaining studies were executed in specialist clinics or private practices (Tables 1 and 2).

The 29 studies using all-ceramic materials included 1225 patients, whereas the 15 studies on metal-ceramic FDPs included 1669 patients. The age of the patients ranged between 16 and 90 years at the time of treatment. The proportion of patients who could not be followed-up for the complete study period was available for 90% of the studies and ranged from 0% to 71%. The mean drop-out rate of patients was 8% for studies reporting on all-ceramic FDPs and 19% for studies on metal-ceramic FDPs (Tables 1 and 2).

### 3.2. FDP survival

For metal-ceramic FDPs, 15 studies provided data on 1796 FDPs after a mean follow-up time of 7.0 years. Out of these, 145 FDPs were reported to be lost. The annual failure rate was estimated at 1.15% (95% CI: 0.72–1.84%) (Fig. 2), translating into a 5-year survival rate for metal-ceramic FDPs of 94.4% (95% CI: 91.2–96.5%) (Table 3).

The results for all-ceramic FDPs was divided split into reconstructions based on reinforced glass ceramic, glass-infiltrated alumina (InCeram Alumina and InCeram Zirconia) and densely sintered zirconia. For reinforced glass ceramic FDPs, 7 studies provided data on 208 FDPs. After a mean follow-up time of 6.0 years, 29 FDPs were reported to be lost. The annual failure rate was estimated at 2.31% (95% CI: 1.23–4.35%) (Fig. 3) translating into a 5-year survival rate for reinforced glass ceramic FDPs of 89.1% (95% CI: 80.4–94.0%) (Table 3). For glass-infiltrated alumina FDPs, 6 studies provided data on 229 FDPs. After a mean follow-up time of 4.1 years, 28 FDPs were reported to be lost. The annual failure rate was estimated at 2.97% (95% CI: 1.20–7.35%) (Fig. 4) translating into a 5-year survival rate for glass-infiltrated alumina FDPs of 86.2% (95% CI: 69.3–94.2%) (Table 3). For densely sintered zirconia FDPs, 16 studies provided data on 673 FDPs from which 62 FDPs were reported to be lost after a mean follow-up time of 4.5 years. The annual failure rate was estimated at 2.02% (95% CI: 1.24–3.31%) (Fig. 5) translating into a 5-year survival rate for densely sintered zirconia FDPs of 90.4% (95% CI: 84.8–94.0%) (Table 3).

At the 5-year follow-up, the annual failure rates of different types of FDPs ranged from 1.15% to 2.97% and the 5-year survival ranged from 86.2% to 94.4%. Investigating formally the relative failure rates of different types of FDPs, using metal-ceramic FDPs as reference, all-ceramic FDPs showed higher annual failure rates. Moreover, for glass-infiltrated alumina FDPs this difference reached statistical significance ( $p = 0.052$ ) (Table 4).

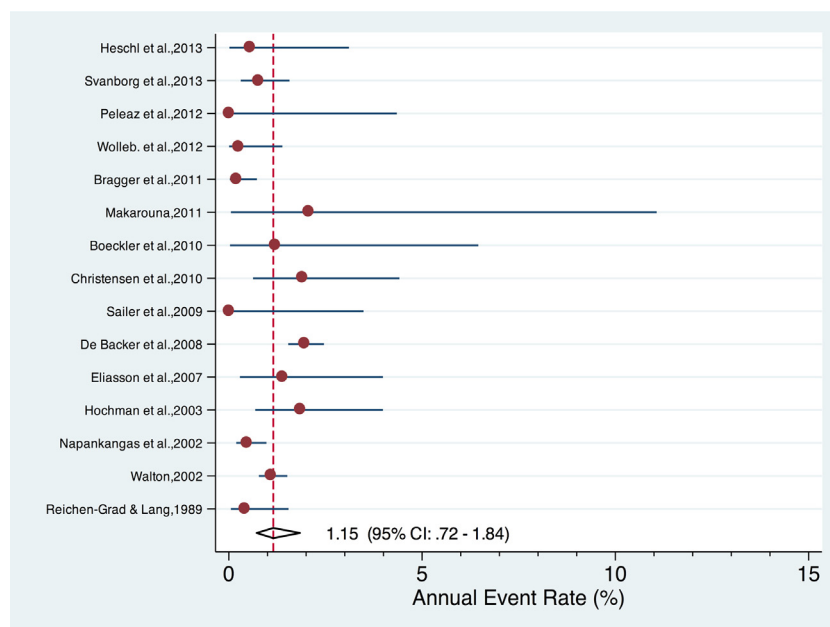


Fig. 2 – Annual failure rate of metal-ceramic FDPs.



**Table 3 – Annual failure rates and survival of metal-ceramic and all-ceramic FDPs.**

| Study                                  | Year of publication | Total no. of FDPs | Mean follow-up time | No. of failure | Total FDPs exposure time | Estimated annual failure rate <sup>a</sup> (per 100 FDP years) | Estimated survival after 5 years <sup>a</sup> (in percent) |
|----------------------------------------|---------------------|-------------------|---------------------|----------------|--------------------------|----------------------------------------------------------------|------------------------------------------------------------|
| <b>Metal ceramic</b>                   |                     |                   |                     |                |                          |                                                                |                                                            |
| Svanborg et al.                        | 2013                | 201               | 4.6                 | 7              | 915                      | 0.77                                                           | 96.2%                                                      |
| Peleaz et al.                          | 2012                | 20                | 4.2                 | 0              | 83                       | 0                                                              | 100%                                                       |
| Wolleb et al.                          | 2012                | 76                | 5.3                 | 1              | 400                      | 0.25                                                           | 98.8%                                                      |
| Heschl et al.                          | 2013                | 28                | 6.3                 | 1              | 177                      | 0.56                                                           | 97.2%                                                      |
| Makarouna                              | 2011                | 19                | 2.5                 | 1              | 48                       | 2.08                                                           | 90.1%                                                      |
| Brägger et al.                         | 2011                | 82                | 12.1                | 2              | 992                      | 0.20                                                           | 99.0%                                                      |
| Christensen and Ploeger                | 2010                | 87                | 3.0                 | 5              | 261                      | 1.92                                                           | 90.9%                                                      |
| Boeckler et al.                        | 2010                | 31                | 2.7                 | 1              | 84                       | 1.19                                                           | 94.2%                                                      |
| Sailer et al.                          | 2009                | 38                | 2.7                 | 0              | 104                      | 0                                                              | 100%                                                       |
| De Backer et al.                       | 2008                | 322               | 11.4                | 72             | 3675                     | 1.96                                                           | 90.7%                                                      |
| Eliasson et al.                        | 2007                | 51                | 4.3                 | 3              | 217                      | 1.38                                                           | 93.3%                                                      |
| Hochman et al.                         | 2003                | 49                | 6.3                 | 6              | 324                      | 1.85                                                           | 91.2%                                                      |
| Walton                                 | 2002                | 515               | 7.4                 | 37             | 3363                     | 1.10                                                           | 94.6%                                                      |
| Napankangas et al.                     | 2002                | 204               | 7.6                 | 7              | 1478                     | 0.47                                                           | 97.7%                                                      |
| Reichen-Grad and Lang                  | 1989                | 73                | 6.4                 | 2              | 465                      | 0.43                                                           | 97.9%                                                      |
| Total                                  |                     | 1796              | 7.0                 | 145            | 12,586                   |                                                                |                                                            |
| Summary estimate (95% CI) <sup>a</sup> |                     |                   |                     |                |                          | 1.15 (0.72–1.84)                                               | 94.4% (91.2–96.5%)                                         |
| <b>Reinforced glass ceramic</b>        |                     |                   |                     |                |                          |                                                                |                                                            |
| Sola-Ruiz et al.                       | 2013                | 21                | 10.0                | 6              | 210                      | 2.86                                                           | 86.7%                                                      |
| Kern et al.                            | 2012                | 36                | 10.1                | 4              | 363                      | 1.10                                                           | 94.6%                                                      |
| Makarouna                              | 2011                | 18                | 4.7                 | 6              | 84                       | 7.14                                                           | 70.0%                                                      |
| Wolfart et al.                         | 2009                | 36                | 6.9                 | 2              | 247                      | 0.81                                                           | 96.0%                                                      |
| Esquivel et al.                        | 2008                | 30                | 3.3                 | 5              | 100                      | 5.00                                                           | 77.9%                                                      |
| Wolfart et al.                         | 2005                | 36                | 4.0                 | 0              | 120                      | 0                                                              | 100%                                                       |
| Marquart et al.                        | 2005                | 31                | 4.2                 | 6              | 129                      | 4.65                                                           | 79.3%                                                      |
| Total                                  |                     | 208               | 6.0                 | 29             | 1253                     |                                                                |                                                            |
| Summary estimate (95% CI) <sup>a</sup> |                     |                   |                     |                |                          | 2.31 (1.23–4.35)                                               | 89.1% (80.4–94.0%)                                         |
| <b>Glass infiltrated alumina</b>       |                     |                   |                     |                |                          |                                                                |                                                            |
| Christensen and Ploeger                | 2010                | 23                | 3.0                 | 11             | 69                       | 15.9                                                           | 45.1%                                                      |
| Eschbach et al.                        | 2009                | 65                | 4.5                 | 2              | 295                      | 0.68                                                           | 96.7%                                                      |
| Suarez et al.                          | 2004                | 18                | 3.0                 | 1              | 53                       | 1.89                                                           | 91.0%                                                      |
| Olsson et al.                          | 2003                | 42                | 6.3                 | 5              | 266                      | 1.88                                                           | 91.0%                                                      |
| van Steyern et al.                     | 2001                | 20                | 5.0                 | 2              | 95                       | 2.11                                                           | 90.0%                                                      |
| Soerensen et al.                       | 1998                | 61                | 3.0                 | 7              | 165                      | 4.24                                                           | 80.9%                                                      |
| Total                                  |                     | 229               | 4.1                 | 28             | 943                      |                                                                |                                                            |
| Summary estimate (95% CI) <sup>a</sup> |                     |                   |                     |                |                          | 2.97 (1.20–7.35)                                               | 86.2% (69.3–94.2%)                                         |
| <b>Densely sintered zirconia</b>       |                     |                   |                     |                |                          |                                                                |                                                            |
| Rinke et al.                           | 2013                | 99                | 6.3                 | 19             | 627                      | 3.03                                                           | 85.9%                                                      |
| Raigrodski et al.                      | 2012                | 20                | 4.7                 | 0              | 94                       | 0                                                              | 100%                                                       |

**Table 3 – (Continued)**

| Study                                  | Year of publication | Total no. of FDPs | Mean follow-up time | No. of failure | Total FDPs exposure time | Estimated annual failure rate <sup>a</sup> (per 100 FDP years) | Estimated survival after 5 years <sup>a</sup> (in percent) |
|----------------------------------------|---------------------|-------------------|---------------------|----------------|--------------------------|----------------------------------------------------------------|------------------------------------------------------------|
| Peleaz                                 | 2012                | 20                | 4.2                 | 1              | 83                       | 1.20                                                           | 94.2%                                                      |
| Lops et al.                            | 2012                | 28                | 6.5                 | 2              | 182                      | 1.10                                                           | 94.7%                                                      |
| Sax et al.                             | 2011                | 57                | 7.6                 | 15             | 433                      | 3.46                                                           | 84.1%                                                      |
| Sorrentino et al.                      | 2011                | 48                | 5.0                 | 0              | 240                      | 0                                                              | 100%                                                       |
| Schmitt et al.                         | 2011                | 15                | 4.0                 | 0              | 60                       | 0                                                              | 100%                                                       |
| Christensen and Ploeger                | 2010                | 80                | 3.0                 | 14             | 240                      | 5.83                                                           | 74.7%                                                      |
| Beuer et al.                           | 2010                | 18                | 2.9                 | 1              | 53                       | 1.89                                                           | 91.0%                                                      |
| Roediger et al.                        | 2010                | 99                | 4.2                 | 7              | 413                      | 1.69                                                           | 91.9%                                                      |
| Sailer et al.                          | 2009                | 38                | 3.2                 | 0              | 121                      | 0                                                              | 100%                                                       |
| Wolfart et al.                         | 2009                | 24                | 4.0                 | 1              | 97                       | 1.03                                                           | 95.0%                                                      |
| Beuer et al.                           | 2009                | 21                | 2.5                 | 2              | 53                       | 3.77                                                           | 82.8%                                                      |
| Edelhoff et al.                        | 2008                | 22                | 3.1                 | 0              | 69                       | 0                                                              | 100%                                                       |
| Molin and Karlsson                     | 2008                | 19                | 5.0                 | 0              | 95                       | 0                                                              | 100%                                                       |
| Tinschert et al.                       | 2008                | 65                | 3.1                 | 0              | 202                      | 0                                                              | 100%                                                       |
| Total                                  |                     | 673               | 4.5                 | 62             | 3062                     |                                                                |                                                            |
| Summary estimate (95% CI) <sup>a</sup> |                     |                   |                     |                |                          | 2.02 (1.24–3.31)                                               | 90.4% (84.8–94.0%)                                         |
| Overall results                        |                     | 2906              | 6.1                 | 264            | 17,844                   |                                                                |                                                            |
| Summary estimate (95% CI) <sup>a</sup> |                     |                   |                     |                |                          | 1.48 (1.11–1.97)                                               | 92.9% (90.6–94.6%)                                         |

<sup>a</sup> Based on robust Poisson regression.

**Table 4 – Summary of annual failure rates, relative failure rates and survival estimates for FDPs with metal-ceramic FDPs as reference.**

| Type of FDPs              | Total number of FDPs | Total FDPs exposure time | Mean FDPs follow-up time | Estimated annual failure rate <sup>*</sup> | 5-Year survival summary estimate <sup>*</sup> (95% CI) | Relative failure rate <sup>**</sup> | p-Value <sup>**</sup> |
|---------------------------|----------------------|--------------------------|--------------------------|--------------------------------------------|--------------------------------------------------------|-------------------------------------|-----------------------|
| Metal-ceramic             | 1796                 | 12,586                   | 7.0                      | 1.15 (0.72–1.84)                           | 94.4% (91.2–96.5%)                                     | 1.00 (Ref.)                         |                       |
| Reinforced glass ceramic  | 208                  | 1253                     | 6.0                      | 2.31 (1.23–4.35)                           | 89.1% (80.4–94.0%)                                     | 2.01 (0.95–4.25)                    | 0.068                 |
| Glass-infiltrated alumina | 229                  | 943                      | 4.1                      | 2.97 (1.20–7.35)                           | 86.2% (69.3–94.2%)                                     | 2.58 (0.99–6.69)                    | 0.052                 |
| Densely sintered zirconia | 673                  | 3062                     | 4.5                      | 2.02 (1.24–3.31)                           | 90.4% (84.8–94.0%)                                     | 1.76 (0.90–3.41)                    | 0.096                 |

<sup>\*</sup> Based on robust Poisson regression.

<sup>\*\*</sup> Based on multivariable robust Poisson regression including all types of FDPs.

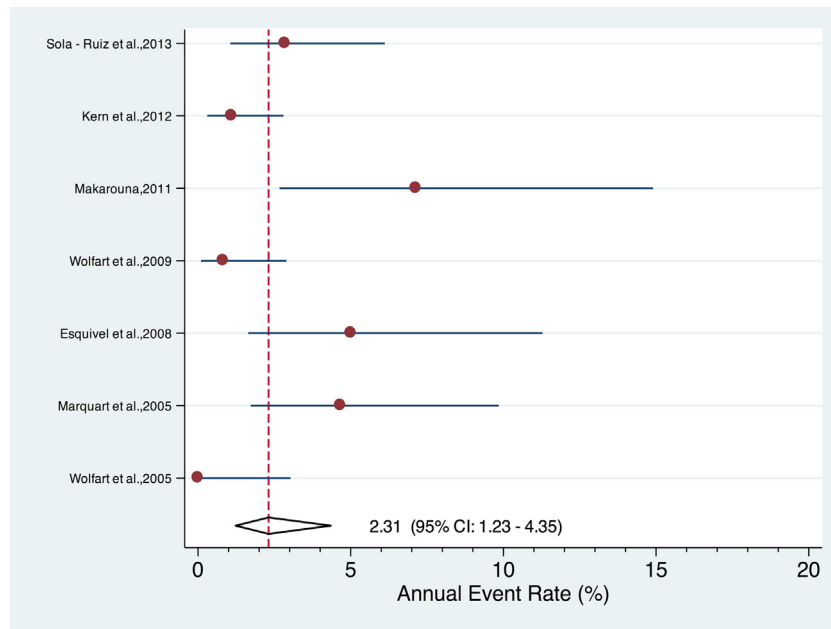


Fig. 3 – Annual failure rate of reinforced glass ceramic FDPs.

### 3.3. Biological complications

#### 3.3.1. Secondary caries

Eighteen studies reported on the incidence of secondary caries on the abutment level. From 3351 FDP abutments included in those studies, 52 abutments developed secondary caries. The overall annual complication rate was 0.29%, translating into a 5-year complication rate of 1.4% (Table 5). For different types of FDPs the annual rate of secondary caries ranged from 0.11% to 0.65%. The lowest annual complication rate 0.11% was reported for reinforced glass ceramic FDPs and the highest complication rate 0.65% was reported for densely sintered

zirconia FDPs. Investigating the relative complication rates of different types of FDPs, using metal-ceramic FDPs as reference, densely sintered zirconia FDPs experienced significantly higher rate of secondary caries ( $p = 0.001$ ) (Table 6).

Information about loss of the entire reconstruction due to secondary caries was given in 38 studies. From 2145 FDPs included in these studies 55 were lost due to secondary caries. The overall annual failure rate was 0.43%, translating into a 5-year failure rate of 2.1% (Table 5). For different types of FDPs the annual rate of failures due to caries ranged from 0.09% to 0.54%. The lowest annual failure rate 0.09% was reported for reinforced glass ceramic FDPs and the highest failure rates

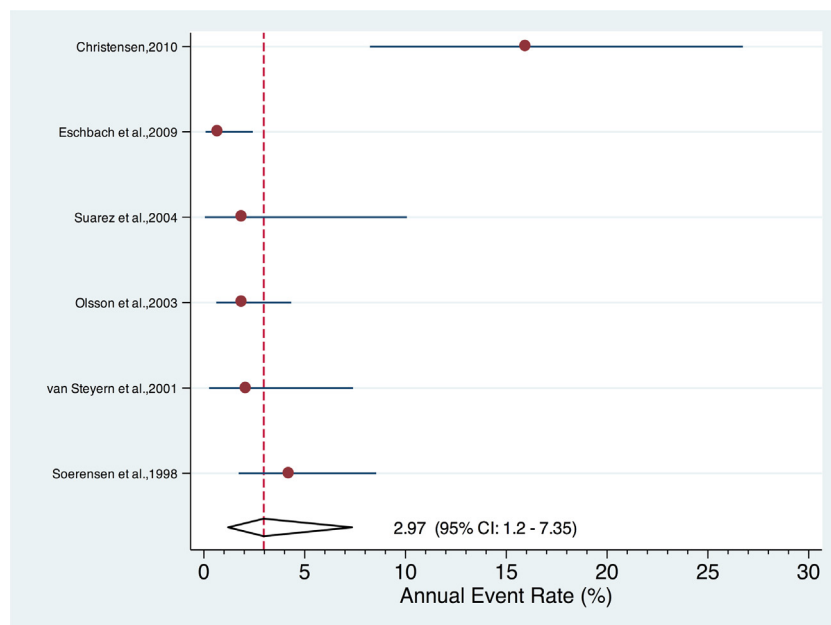


Fig. 4 – Annual failure rate of glass-infiltrated alumina FDPs.

Table 5 – Overview of biological and technical complications of different types of FDPs.

| Complication                                   | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) |
|------------------------------------------------|-----------------------------------|-------------------------------------------------------|--------------------------------------------------------|-----------------------------------|-------------------------------------------------------|--------------------------------------------------------|-----------------------------------|-------------------------------------------------------|--------------------------------------------------------|
|                                                | Overall results – all FDPs        |                                                       |                                                        | Metal ceramic FDPs                |                                                       |                                                        | Reinforced glass ceramic FDPs     |                                                       |                                                        |
| Caries on abutments                            | 3351                              | 0.29 <sup>+</sup> (0.14–2.94)                         | 1.4% <sup>+</sup> (0.7–2.9%)                           | 2497                              | 0.24 <sup>+</sup> (0.10–0.57)                         | 1.2% <sup>+</sup> (0.5–2.8%)                           | 199                               | 0.11 <sup>+</sup> (0.01–0.94)                         | 0.5% <sup>+</sup> (0.06–4.6%)                          |
| FDPs lost due to caries                        | 2145                              | 0.43 <sup>+</sup> (0.21–0.88)                         | 2.1% <sup>+</sup> (1.1–4.3%)                           | 1053                              | 0.54 <sup>+</sup> (0.24–1.22)                         | 2.7% <sup>+</sup> (1.2–5.9%)                           | 190                               | 0.09 <sup>+</sup> (0.01–0.76)                         | 0.4% <sup>+</sup> (0.05–3.7%)                          |
| FDPs lost due to<br>periodontal disease        | 2096                              | 0.23 <sup>+</sup> (0.10–0.54)                         | 1.2% <sup>+</sup> (0.5–2.7%)                           | 1004                              | 0.06 <sup>+</sup> (0.03–0.11)                         | 0.3% <sup>+</sup> (0.1–0.6%)                           | 190                               | 0.60 <sup>+</sup> (0.10–3.52)                         | 2.9% <sup>+</sup> (0.5–16.1%)                          |
| FDPs lost due to<br>abutment tooth<br>fracture | 2107                              | 0.17 <sup>+</sup> (0.12–0.25)                         | 0.9% <sup>+</sup> (0.6–1.3%)                           | 1053                              | 0.19 <sup>+</sup> (0.11–0.30)                         | 0.9% <sup>+</sup> (0.6–1.5%)                           | 190                               | 0.09 <sup>+</sup> (0.02–0.44)                         | 0.4% <sup>+</sup> (0.1–2.2%)                           |
| Loss of abutment tooth<br>vitality             | 243                               | 0.44 <sup>+</sup> (0.11–1.80)                         | 2.2% <sup>+</sup> (0.5–8.6%)                           | n.a.                              | n.a.                                                  | n.a.                                                   | n.a.                              | n.a.                                                  | n.a.                                                   |
| Marginal discolorations                        | 253                               | 3.91 <sup>+</sup> (1.46–10.46)                        | 17.7% <sup>+</sup> (7.0–40.7%)                         | 20                                | 4.82 <sup>+</sup> (1.33–11.88)                        | 21.4% <sup>+</sup> (6.4–44.8%)                         | 118                               | 0.72 <sup>+</sup> (0.23–2.19)                         | 3.5% <sup>+</sup> (1.2–10.4%)                          |
| Framework fracture                             | 2640                              | 0.45 <sup>+</sup> (0.25–0.82)                         | 2.2% <sup>+</sup> (1.2–4.0%)                           | 1530                              | 0.12 <sup>+</sup> (0.04–0.40)                         | 0.6% <sup>+</sup> (0.2–2.0%)                           | 208                               | 1.68 <sup>+</sup> (0.84–3.33)                         | 8.0% <sup>+</sup> (4.1–15.3%)                          |
| Ceramic fractures                              | 2129                              | 1.56 <sup>+</sup> (0.85–2.86)                         | 7.5% <sup>+</sup> (4.2–13.3%)                          | 1305                              | 1.03 <sup>+</sup> (0.42–2.56)                         | 5.0% <sup>+</sup> (2.1–12.0%)                          | 187                               | 1.34 <sup>+</sup> (0.99–1.82)                         | 6.5% <sup>+</sup> (4.8–8.7%)                           |
| Ceramic chipping                               | 1659                              | 2.71 <sup>+</sup> (1.52–4.83)                         | 12.7% <sup>+</sup> (7.3–21.4%)                         | 781                               | 1.79 <sup>+</sup> (0.81–3.96)                         | 8.6% <sup>+</sup> (4.0–18.0%)                          | 213                               | 1.07 <sup>+</sup> (0.48–2.36)                         | 5.2% <sup>+</sup> (2.4–11.1%)                          |
| Loss of retention                              | 1702                              | 0.64 <sup>+</sup> (0.35–1.16)                         | 3.1% <sup>+</sup> (1.7–5.6%)                           | 955                               | 0.42 <sup>+</sup> (0.16–1.09)                         | 2.1% <sup>+</sup> (0.8–5.3%)                           | 142                               | 0.58 <sup>+</sup> (0.35–0.97)                         | 2.9% <sup>+</sup> (1.7–4.7%)                           |
| Complication                                   | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) | Number of<br>abutments or<br>FDPs | Estimated<br>annual<br>complication<br>rates (95% CI) | Cumulative<br>5-year<br>complication<br>rates (95% CI) |
|                                                | Glass-infiltrated alumina FDPs    |                                                       |                                                        |                                   | Densely sintered zirconia FDPs                        |                                                        |                                   |                                                       |                                                        |
| Caries on abutments                            | 168                               | 0.41 <sup>+</sup> (0.22–0.74)                         | 2.0% <sup>+</sup> (1.1–3.6%)                           | 487                               | 0.65 <sup>+</sup> (0.27–1.56)                         | 3.2% <sup>+</sup> (1.3–7.5%)                           |                                   |                                                       |                                                        |
| FDPs lost due to caries                        | 229                               | 0.11 <sup>+</sup> (0.02–0.56)                         | 0.5% <sup>+</sup> (0.1–2.8%)                           | 673                               | 0.39 <sup>+</sup> (0.20–0.77)                         | 1.9% <sup>+</sup> (1.0–3.8%)                           |                                   |                                                       |                                                        |
| FDPs lost due to<br>periodontal disease        | 229                               | 1.59 <sup>+</sup> (0.62–4.08)                         | 7.6% <sup>+</sup> (3.1–18.4%)                          | 673                               | 0.10 <sup>+</sup> (0.03–0.30)                         | 0.5% <sup>+</sup> (0.2–1.5%)                           |                                   |                                                       |                                                        |
| FDPs lost due to<br>abutment tooth<br>fracture | 229                               | 0.11 <sup>+</sup> (0.01–1.02)                         | 0.5% <sup>+</sup> (0.05–5.0%)                          | 635                               | 0.21 <sup>+</sup> (0.11–0.38)                         | 1.0% <sup>+</sup> (0.6–1.9%)                           |                                   |                                                       |                                                        |
| Loss of abutment tooth<br>vitality             | n.a.                              | n.a.                                                  | n.a.                                                   | 243                               | 0.44 <sup>+</sup> (0.11–1.80)                         | 2.2% <sup>+</sup> (0.5–8.6%)                           |                                   |                                                       |                                                        |
| Marginal discolorations                        | 18                                | 3.77 <sup>+</sup> (0.46–12.98)                        | 17.2% <sup>+</sup> (2.3–47.7%)                         | 97                                | 6.72 <sup>+</sup> (3.30–13.68)                        | 28.5% <sup>+</sup> (15.2–49.5%)                        |                                   |                                                       |                                                        |
| Framework fracture                             | 229                               | 2.76 <sup>+</sup> (1.01–7.52)                         | 12.9% <sup>+</sup> (4.9–31.3%)                         | 673                               | 0.39 <sup>+</sup> (0.24–0.65)                         | 1.9% <sup>+</sup> (1.2–3.2%)                           |                                   |                                                       |                                                        |
| Ceramic fractures                              | 65                                | 1.36 <sup>+</sup> (0.37–3.44)                         | 6.6% <sup>+</sup> (1.8–15.8%)                          | 572                               | 3.14 <sup>+</sup> (2.37–4.17)                         | 14.5% <sup>+</sup> (11.2–18.8%)                        |                                   |                                                       |                                                        |
| Ceramic chipping                               | 90                                | 7.55 <sup>+</sup> (1.09–52.24)                        | 31.4% <sup>+</sup> (5.3–92.7%)                         | 575                               | 4.33 <sup>+</sup> (1.93–9.72)                         | 19.5% <sup>+</sup> (9.2–38.5%)                         |                                   |                                                       |                                                        |
| Loss of retention                              | 107                               | 0.53 <sup>+</sup> (0.31–0.93)                         | 2.6% <sup>+</sup> (1.5–4.5%)                           | 498                               | 1.28 <sup>+</sup> (0.83–1.97)                         | 6.2% <sup>+</sup> (4.1–9.4%)                           |                                   |                                                       |                                                        |
| n.a., “not available”.                         |                                   |                                                       |                                                        |                                   |                                                       |                                                        |                                   |                                                       |                                                        |
| * Based on robust Poisson regression.          |                                   |                                                       |                                                        |                                   |                                                       |                                                        |                                   |                                                       |                                                        |

**Table 6 – Relative complication rates for different types of FDPs.**

| Type of complications                      | Metal ceramic FDPs | Reinforced glass ceramic FDPs     |                      | Glass-infiltrated alumina FDPs    |                      | Densely sintered zirconia FDPs    |                      |
|--------------------------------------------|--------------------|-----------------------------------|----------------------|-----------------------------------|----------------------|-----------------------------------|----------------------|
|                                            |                    | Relative compl. rate <sup>*</sup> | p-Value <sup>*</sup> | Relative compl. rate <sup>*</sup> | p-Value <sup>*</sup> | Relative compl. rate <sup>*</sup> | p-Value <sup>*</sup> |
| Carries on abutments                       | 1.00 (Ref.)        | 0.45 (0.06–3.29)                  | 0.432                | 1.73 (0.53–5.63)                  | 0.366                | 2.75 (1.50–5.07)                  | 0.001                |
| FDPs lost due to caries                    | 1.00 (Ref.)        | 0.16 (0.02–1.37)                  | 0.095                | 0.19 (0.03–1.10)                  | 0.064                | 0.72 (0.26–2.01)                  | 0.535                |
| FDPs lost due to periodontal disease       | 1.00 (Ref.)        | 10.8 (1.82–64.31)                 | 0.009                | 28.80 (9.45–87.74)                | <0.0001              | 1.77 (0.49–6.44)                  | 0.384                |
| FDPs lost due to abutment tooth fracture   | 1.00 (Ref.)        | 0.46 (0.09–2.26)                  | 0.341                | 0.57 (0.07–4.92)                  | 0.612                | 1.11 (0.52–2.38)                  | 0.784                |
| Marginal discolorations                    | 1.00 (Ref.)        | 0.14 (0.05–0.42)                  | <0.0001              | 0.78 (0.78–0.78)                  | <0.0001              | 1.39 (0.75–2.58)                  | 0.289                |
| Framework fracture                         | 1.00 (Ref.)        | 13.81 (3.65–52.28)                | <0.0001              | 22.72 (5.13–100.69)               | <0.0001              | 3.23 (0.91–11.42)                 | 0.069                |
| Ceramic fractures (Chipping and fractures) | 1.00 (Ref.)        | 1.30 (0.52–3.28)                  | 0.578                | 1.31 (0.54–3.18)                  | 0.544                | 3.05 (1.21–7.69)                  | 0.018                |
| Ceramic chipping                           | 1.00 (Ref.)        | 0.60 (0.21–1.72)                  | 0.338                | 4.21 (0.71–24.92)                 | 0.113                | 2.42 (0.81–7.25)                  | 0.115                |
| Loss of retention                          | 1.00 (Ref.)        | 1.40 (0.50–3.88)                  | 0.523                | 1.28 (0.48–3.47)                  | 0.621                | 3.07 (1.12–8.37)                  | 0.028                |

\* Based on multivariable robust Poisson regression including all types of FDPs with metal ceramic FDPs as reference.

0.39% and 0.54% for densely sintered zirconia FDPs and metal-ceramic FDPs, respectively. The difference between different types of FDPs did not reach statistical significance ( $p = 0.064$ ,  $0.095$  &  $0.535$ ) (Table 6).

### 3.3.2. Loss of vitality

Loss of abutment vitality was reported in three studies. All of them reporting on densely sintered zirconia FDPs. Four out of 243 abutment teeth, reported to be vital at the time of cementation, presented loss of pulp vitality during the observation period. The annual complication rate was 0.44%, translating into a 5-year complication rate of 2.2% (Table 5).

### 3.3.3. Abutment tooth fracture

The incidence of FDPs lost due to fracture of abutment teeth was reported in 36 studies evaluating 2107 FDPs, out of which 22 were lost. The overall annual failure rate was 0.17%, translating into a 5-year failure rate of 0.9% (Table 5). For different types of FDPs the annual failure rates due to abutment tooth fractures ranged from 0.09% to 0.21%. The difference between different types of FDPs did not reach statistical significance ( $p = 0.341$ ,  $0.612$  &  $0.784$ ) (Table 6).

### 3.3.4. Periodontal disease

The incidence of FDPs lost due to recurrent periodontal disease, was reported in 37 studies evaluating 2096 FDPs, out of which 29 were lost. The overall annual failure rate was 0.23%, translating into a 5-year failure rate of 1.2% (Table 5). For different types of FDPs, the annual failure rates due to recurrent periodontal diseases ranged from 0.06% to 1.59%. The highest annual failure rate was reported for reinforced glass ceramic FDPs 0.60% and glass-infiltrated alumina FDPs 1.59%, translating into a 5 years failure rates of 2.9% and 7.6%, respectively (Table 5). Investigating the relative complication rates of different types of FDPs, using metal-ceramic FDPs as reference, significantly more glass-infiltrated alumina FDPs and reinforced glass ceramic FDPs were lost due to recurrent periodontal diseases ( $p < 0.0001$  &  $0.009$ ).

## 3.4. Technical complications

### 3.4.1. Material complications: framework fracture, ceramic chipping or ceramic fracture

The incidence of framework fracture was reported in 43 out of the 44 studies included in the present systematic review. From 2640 FDPs that were evaluated, 72 were known to be lost due to framework fractures. The overall annual failure rate was 0.45%, translating into a 5-year failure rate of 2.2% (Table 5). For different types of FDPs, the annual failure rates of framework fractures ranged from 0.12% to 2.76%. The highest annual failure rate was reported for reinforced glass ceramic FDPs (1.68%) and glass-infiltrated alumina FDPs (2.76%), translating into a 5-year failure rates of 8.0% and 12.9%, respectively (Table 5). Investigating the relative complication rates of different types of FDPs, using metal-ceramic FDPs as reference, significantly more glass-infiltrated alumina FDPs and reinforced glass ceramic FDPs were lost due to framework fractures ( $p < 0.0001$ ). Compared to the other ceramics, densely sintered zirconia exhibited the highest stability as framework material with an estimated 5-year failure rate of 1.9% (Table 5).

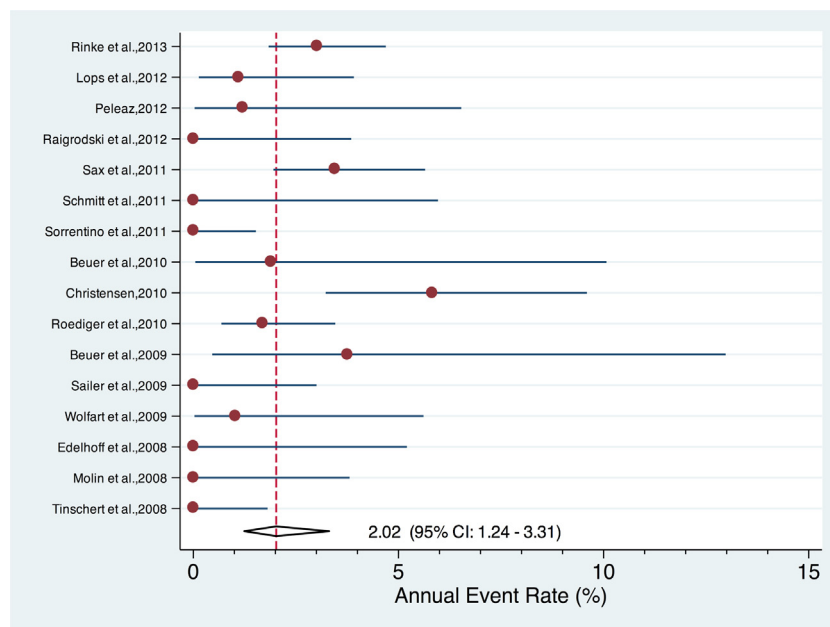


Fig. 5 – Annual failure rate of densely sintered zirconia FDPs.

The incidence, however, of fractures of the ceramic veneering that needed repair or replacement was highest for densely sintered zirconia FDPs with an annual complication rate of 3.14%, translating into a 5-year complication rate of 14.5%. This difference reached statistical significance ( $p = 0.018$ ) (Table 6). For other types of FDPs the annual rate of ceramic fractures ranged from 1.03% to 1.36%, translating into a 5-year complication rate of 5.0–6.5% (Table 6). The incidence of ceramic chipping that could be solved with polishing was reported in 32 studies including 1659 FDPs. The overall annual complication rate was 2.71%, translating into a 5-year complication rate of 12.7% (Table 5). For different types of FDPs, the annual complication rates ranged from 1.07% to 7.55%. Ceramic chipping was the most frequent technical complication reported, but the difference in ceramic chipping between different types of FDPs did not reach statistical significance ( $p = 0.338$ , 0.113 & 0.115).

#### 3.4.2. Loss of retention

Loss of retention or fracture of the luting cement was analyzed in 25 studies reporting on 1702 FDPs. The overall annual complication rate was 0.64%, translating into a 5-year failure rate of 3.1% (Table 5). Densely sintered zirconia FDPs experienced statistically significantly ( $p = 0.028$ ) (Table 6) more retention loss than the other types of FDPs with an annual complication rate of 1.28% and a 5-year complication rate of 6.2%. For other types of FDPs the annual complication rates ranged from 0.42% to 0.58%, translating into a 5-year failure rates of 2.1–2.9% (Table 5).

#### 3.4.3. Marginal discoloration

Marginal discoloration or the occurrence of marginal gaps was evaluated in 9 studies reporting on 253 FDPs. The overall annual complication rate was 3.91%, translating into a 5-year complication rate of 17.7% (Table 5). The lowest incidence of marginal discoloration was seen for reinforced glass ceramic

with annual complication rate of 0.72% or a 5-year complication rate of 3.5%. For the other three types of FDPs, the annual rates of marginal discoloration ranged between 3.77% and 6.72% with the highest incidence reported for densely sintered zirconia FDPs, representing a 5-year complication rate of 28.5% (Table 5).

## 4. Discussion

Systematic reviews have been used extensively in medicine for the last two decades to summarize the cumulative information on the optimal treatment for clinically relevant questions and to support the clinicians in the decision-making process for different treatment options. This research method has slowly found its way into dental research. Systematic reviews have mainly been used to analyze and summarize results from randomized controlled clinical trials (RCTs) [30]. In the absence of RCTs with adequate statistical power to compare head-to-head metal-ceramic and all-ceramic fixed dental prosthesis (FDPs) prospective and retrospective cohort studies and case series with stringent inclusion criteria were included in this systematic review in order to summarize the available information about survival and complication rates of metal-ceramic and all-ceramic FDPs after a observation period of at least 3 years. Even with follow-up periods of at least 3 years, some clinicians may argue that such a period is still too short to obtain reliable information on survival and complication rates of fixed reconstructions. Due to the fact that the use of all-ceramic FDPs is relatively recent, a mean follow-up period of 3 years or more was a necessary compromise.

However it was interesting to see that the median year of publication was 2010 for metal-ceramic FDPs compared with 2009 for all-ceramic FDPs. In a systematic review on the same topic published in the year 2007 by the same authors, only five studies on metal-ceramic FDPs fulfilled the inclusion criteria's



and only one of them was published before the year 2000 [1]. This must be considered peculiar as metal-ceramic FDPs have been considered the golden standard in reconstructive dentistry over decades. A positive shift has to be noticed, as 15 studies reporting on metal-ceramic could be included in the present systematic review.

Survival was defined as FDP remaining in situ with or without modifications and success was defined as the FDPs remaining in situ free of all complications over the entire observation period. From the Forrest plots of study specific failure rates, it is evident that these vary widely among the various studies. This may be attributable to the patient cohort observed, the design and extent of the FDPs, the maintenance care provided and the experience and clinical set-up of the clinicians.

After an observation period of 3 years, the lowest failure rate were observed for metal-ceramic FDPs (5.6%) compared with a failure rates of 9.6% for densely sintered zirconia ceramic FDPs, 10.9% for reinforced glass ceramic FDPs and 13.8% for glass-infiltrated alumina FDPs. Due to the different composition of different ceramic materials it was decided not to pull, different types of all-ceramic FDPs, into one group in the meta-analysis as was done in the previous review on the same topic. Four of the included studies randomized the patients according to material utilized. Three of them reported more failure of all-ceramic FDPs compared with metal-ceramic FDPs [19,31,32]. The last one reported no failures in either group [17].

The most frequent reason for failure of reinforced glass ceramic FDPs and glass-infiltrated alumina FDPs over the 3 years observation period was fracture of the reconstruction framework, reported for 8.0% and 17.2% of the reconstructions respectively. This technical failure was frequently related to using reinforced glass ceramic FDPs and glass-infiltrated alumina FDPs in the posterior area and where the diameter of the connectors was reduced below 4 mm × 4 mm [33]. It has also been argued that all-ceramic FDPs suffer more often from parafunctional habits and malocclusion leading to framework fractures [34]. The framework fracture failure rate was rarer for metal-ceramic FDPs (0.6%) and densely sintered zirconia ceramic FDPs (1.9%). One aspect to consider for all-ceramic FDPs might be the length of the reconstruction. Studies demonstrated a higher rate of framework fractures with an increasing FDP length [35,36].

The most frequent technical complication was chipping of the veneering ceramic with an overall complication rate of 12.7% after 3-year observation period. The incidence of this complication ranged from 6.6% to 31.4% depending on the material type and was most frequently seen by glass-infiltrated alumina FDPs and densely sintered zirconia FDPs. Ceramic chippings for metal-ceramic FDPs appear to occur more frequently during the first year in function. The rate of chippings may then slightly decrease [23]. The high incidence of chipping by densely sintered zirconia FDPs, may be due to the fact that the first generation of zirconia FDPs was made before special low-fusing ceramics with a thermal expansion coefficient compatible with zirconia had been developed. Another reason for this might be the difficulty of getting correct uniform thickness of the virtually designed

frameworks, which may not provide proper support to the veneering ceramic.

Marginal discoloration was, with the exception of reinforced glass ceramic FDPs (3.5%), a frequent technical complication reported for all-ceramic FDPs and metal-ceramic FDPs, ranging from 17.2% to 28.5%. The drawback of this analysis was that it is based on very few observations for metal-ceramic and glass-infiltrated alumina FDPs representing in a very wide confidence interval. In the two studies using a pressed glass-ceramic no discoloration was found [37,38]. This can partly be explained by the manufacturing procedures of the frameworks. The high precision of the manufacturing technique of pressable glass-ceramics has been documented in several investigations [39–41]. Among the studies reporting on marginal discoloration of densely sintered zirconia ceramic FDPs, there was a clear outlier using a prototype CAM-system reporting the highest rate of gaps or discoloration [36]. A possible explanation could be the misfit of these prototype frameworks. In a RCT comparing metal-ceramic and densely sintered zirconia FDPs [17], the fit of the frameworks was analyzed prior to the insertion of the reconstruction [42]. It was demonstrated that milled zirconia frameworks exhibited larger internal gaps than those constructed using conventional metal-ceramic techniques. This larger misfit of CAD/CAM reconstruction can explain a rather high rate of marginal discoloration.

With the exception of caries on abutment level by densely sintered zirconia ceramic FDPs (3.2%) and FDPs lost due to periodontal disease by glass-infiltrated alumina FDPs (7.6%) was the incidence of biological complications such as caries on abutment level, FDPs lost due to caries, FDPs lost due to periodontal disease, FDPs lost due to abutment tooth fracture and loss of abutment tooth vitality relative rare, ranging from 0.3% to 2.9% (Table 5).

When densely sintered zirconia was first introduced as framework material, its excellent physical properties led to the assumption that it may successfully be used to replace the conventional metal-ceramic FDP. The zirconia has been proven to be a strong framework material with low incidence of framework fracture. Specially if not used for long edentulous spans (3 teeth or more) and criteria's for connector dimension are respected. One the other hand, there are still issues with fit and framework design. The present systematic review has demonstrated that problems such as discolorations, secondary caries and loss of retentions, that can be directly related to semi optimal fit are more frequent by densely sintered zirconia FDPs compared with metal-ceramic FDPs and other types of all-ceramic FDPs. Moreover, high incidence of ceramic fractures and chipping is another issue that has taken into account utilizing densely sintered zirconia FDPs.

In this review stringent study inclusion criteria were used. Only studies with a clinical follow-up examination of at least 3 years were included to avoid the potential inaccuracies in event description in studies that based their analysis on patient self-reports. Clearly, a limitation of the present review is the assumption of a constant annual event rate throughout follow-up time after reconstruction. Interpreting the results it must be kept in mind that the mean observation period was on average 7.0 years for metal-ceramic FDPs, and only

4.7 years for all-ceramic FDPs. If the annual failure rates were higher in the years 5–10 than in the years 0–5, then average annual failure rates would be automatically higher for those reconstruction types for which studies with longer follow-up were available. To reduce the impact of such a bias, the results of the present analysis were restricted to estimating the 5-year survival. Another limitation of this review is that it was mainly based on studies that were conducted in an institutional environment, such as university or specialized implant clinics. Therefore, the long-term outcomes observed, cannot be generalized to dental services provided in private practice.

## 5. Conclusion

Metal-ceramic FDPs had lower failure rates than all-ceramic FDPs after a mean observation period of at least 3 years. Framework fractures were frequently reported for reinforced glass ceramic and glass-infiltrated alumina FDPs. Densely sintered zirconia was significantly more stable as framework material, but misfit lead to complications such as discolorations, secondary caries and loss of retention. Moreover, ceramic fractures and chipping of ceramics were frequent. In the future, further refinements in the production of all-ceramic reconstructions are indicated.

## Conflict of interest

The authors do report to have no conflict of interest.

## Acknowledgments

The authors are grateful to Kristin Heimisdóttir, Ásta Óskarsdóttir and Gisela Müller, Study Monitor, Clinic of Fixed and Removable Prosthodontics and Dental Material Science, University of Zurich, for their help in the preparation of the manuscript.

## Excluded studies and reasons for exclusion.

[23] Behr M, Winklhofer C, Schreier M, Zeman F, Kobeck C, Brauer I, et al. Risk of chipping or facings failure of metal ceramic fixed partial prostheses—a retrospective data record analysis. *Clin Oral Invest* 2012;16:401–5. **Reason for exclusion: chart review.**

[24] De Backer H, Van Maele G, De Moor N, Van den Berghe L. The influence of gender and age on fixed prosthetic restoration longevity: an up to 18- to 20-year follow-up in an undergraduate clinic. *Int J Prosthodont* 2007;20:579–86. **Reason for exclusion: multiple publications on same patient cohort.**

[25] De Backer H, Van Maele G, De Moor N, Van den Berghe L. Long-term results of short-span versus long-span fixed dental prostheses: an up to 20-year retrospective study. *Int J Prosthodont* 2008;21:75–85. **Reason for exclusion: multiple publications on same patient cohort.**

[26] Pelaez J, Cogolludo PG, Serrano B, Lozano JF, Suarez MJ. A prospective evaluation of zirconia posterior fixed dental prostheses: three-year clinical results. *J Prosthet Dent*

2012;107:373–9. **Reason for exclusion: multiple publication on same patient cohort.**

[27] Reitemeier B, Hansel K, Kastner C, Weber A, Walter MH. A prospective 10-year study of metal ceramic single crowns and fixed dental prosthesis retainers in private practice settings. *J Prosthet Dent* 2013;109:149–55. **Reason for exclusion: no data for FDPs, only abutments.**

[28] Sailer I, Feher A, Filser F, Gauckler LJ, Luthy H, Hammerle CH. Five-year clinical results of zirconia frameworks for posterior fixed partial dentures. *Int J Prosthodont* 2007;20:383–8. **Reason for exclusion: multiple publications on same patient cohort.**

[29] Walton TR. Changes in the outcome of metal-ceramic tooth-supported single crowns and FDPs following the introduction of osseointegrated implant dentistry into a prosthodontic practice. *Int J Prosthodont* 2009;22:260–7. **Reason for exclusion: multiple publications on same patient cohort.**

## REFERENCES

- [1] Sailer I, Pjetursson BE, Zwahlen M, Hammerle CH. A systematic review of the survival and complication rates of all-ceramic and metal-ceramic reconstructions after an observation period of at least 3 years. Part II: Fixed dental prostheses. *Clin Oral Implants Res* 2007;18(Suppl. 3):86–96.
- [2] Pihlgren K, Forsberg H, Sjödin L, Lundgren P, Wanman A. Changes in tooth mortality between 1990 and 2002 among adults in Vasterbotten County, Sweden: influence of socioeconomic factors, general health, smoking, and dental care habits on tooth mortality. *Swed Dent J* 2011;35:77–88.
- [3] Pjetursson BE, Thoma D, Jung R, Zwahlen M, Zembic A. A systematic review of the survival and complication rates of implant-supported fixed dental prostheses (FDPs) after a mean observation period of at least 5 years. *Clin Oral Implants Res* 2012;23(Suppl. 6):22–38.
- [4] Jung RE, Zembic A, Pjetursson BE, Zwahlen M, Thoma DS. Systematic review of the survival rate and the incidence of biological, technical, and aesthetic complications of single crowns on implants reported in longitudinal studies with a mean follow-up of 5 years. *Clin Oral Implants Res* 2012;23(Suppl. 6):2–21.
- [5] Raigrodski AJ, Hillstead MB, Meng GK, Chung KH. Survival and complications of zirconia-based fixed dental prostheses: a systematic review. *J Prosthet Dent* 2012;107:170–7.
- [6] Tan K, Pjetursson BE, Lang NP, Chan ES. A systematic review of the survival and complication rates of fixed partial dentures (FPDs) after an observation period of at least 5 years. *Clin Oral Implants Res* 2004;15:654–66.
- [7] Olsson KG, Furst B, Andersson B, Carlsson GE. A long-term retrospective and clinical follow-up study of In-ceram alumina FPDs. *Int J Prosthodont* 2003;16:150–6.
- [8] Raigrodski AJ, Chiche GJ, Swift Jr EJ. All-ceramic fixed partial dentures. Part III: Clinical studies. *J Esthet Restor Dent* 2002;14:313–9.
- [9] Wolfart S, Eschbach S, Scherrer S, Kern M. Clinical outcome of three-unit lithium-disilicate glass-ceramic fixed dental prostheses: up to 8 years results. *Dent Mater* 2009;25:e63–71.
- [10] Borba M, de Araujo MD, de Lima E, Yoshimura HN, Cesar PF, Griggs JA, et al. Flexural strength and failure modes of layered ceramic structures. *Dent Mater* 2011;27:1259–66.
- [11] Zimmer D, Gerds T, Strub JR. Survival rate of IPS-Empress 2 all-ceramic crowns and bridges: three year's results. *Schweiz Monatsschr Zahnmed* 2004;114:115–9.

- [12] Christel P, Meunier A, Heller M, Torre JP, Peille CN. Mechanical properties and short-term in-vivo evaluation of yttrium-oxide-partially-stabilized zirconia. *J Biomed Mater Res* 1989;23:45–61.
- [13] Guazzato M, Albakry M, Ringer SP, Swain MV. Strength, fracture toughness and microstructure of a selection of all-ceramic materials. Part II. Zirconia-based dental ceramics. *Dent Mater* 2004;20:449–56.
- [14] Salido MP, Martinez-Rus F, del Rio F, Pradies G, Ozcan M, Suarez MJ. Prospective clinical study of zirconia-based posterior four-unit fixed dental prostheses: four-year follow-up. *Int J Prosthodont* 2012;25:403–9.
- [15] Schmitt J, Goellner M, Lohbauer U, Wichmann M, Reich S. Zirconia posterior fixed partial dentures: 5-year clinical results of a prospective clinical trial. *Int J Prosthodont* 2012;25:585–9.
- [16] Vigolo P, Mutinelli S. Evaluation of zirconium-oxide-based ceramic single-unit posterior fixed dental prostheses (FDPs) generated with two CAD/CAM systems compared to porcelain-fused-to-metal single-unit posterior FDPs: a 5-year clinical prospective study. *J Prosthodont* 2012;21:265–9.
- [17] Sailer I, Gottnerb J, Kanelb S, Hammerle CH. Randomized controlled clinical trial of zirconia-ceramic and metal-ceramic posterior fixed dental prostheses: a 3-year follow-up. *Int J Prosthodont* 2009;22:553–60.
- [18] Swain MV. Unstable cracking (chipping) of veneering porcelain on all-ceramic dental crowns and fixed partial dentures. *Acta Biomater* 2009;5:1668–77.
- [19] Christensen RP, Ploeger BJ. A clinical comparison of zirconia, metal and alumina fixed-prosthesis frameworks veneered with layered or pressed ceramic: a three-year report. *J Am Dent Assoc* 2010;141:1317–29.
- [20] Diniz AC, Nascimento RM, Souza JC, Henriques BB, Carreiro AF. Fracture and shear bond strength analyses of different dental veneering ceramics to zirconia. *Mater Sci Eng C: Mater Biol Appl* 2014;38:79–84.
- [21] Kirkwood BR, Sterne JAC. *Essential Medical Statistics*, Chapter 26: Survival Analysis: Displaying and Comparing Survival Patterns. Oxford: Blackwell Science Ltd.; 2003.
- [22] Kirkwood BR, Sterne JAC. *Medical Statistics*, Chapter 24: Poisson Regression. Oxford: Blackwell Science Ltd; 2003.
- [23] Behr M, Winklhofer C, Schreier M, Zeman F, Kobeck C, Brauer I, et al. Risk of chipping or facings failure of metal ceramic fixed partial prostheses – a retrospective data record analysis. *Clin Oral Investig* 2012;16:401–5.
- [24] De Backer H, Van Maele G, De Moor N, Van den Berghe L. The influence of gender and age on fixed prosthetic restoration longevity: an up to 18- to 20-year follow-up in an undergraduate clinic. *Int J Prosthodont* 2007;20:579–86.
- [25] De Backer H, Van Maele G, De Moor N, Van den Berghe L. Long-term results of short-span versus long-span fixed dental prostheses: an up to 20-year retrospective study. *Int J Prosthodont* 2008;21:75–85.
- [26] Pelaez J, Cogolludo PG, Serrano B, Lozano JF, Suarez MJ. A prospective evaluation of zirconia posterior fixed dental prostheses: three-year clinical results. *J Prosthet Dent* 2012;107:373–9.
- [27] Reitemeier B, Hansel K, Kastner C, Weber A, Walter MH. A prospective 10-year study of metal ceramic single crowns and fixed dental prosthesis retainers in private practice settings. *J Prosthet Dent* 2013;109:149–55.
- [28] Sailer I, Feher A, Filser F, Gauckler LJ, Luthy H, Hammerle CH. Five-year clinical results of zirconia frameworks for posterior fixed partial dentures. *Int J Prosthodont* 2007;20:383–8.
- [29] Walton TR. Changes in the outcome of metal-ceramic tooth-supported single crowns and FDPs following the introduction of osseointegrated implant dentistry into a prosthodontic practice. *Int J Prosthodont* 2009;22:260–7.
- [30] Egger M, Smith GD, Sterne JA. Uses and abuses of meta-analysis. *Clin Med* 2001;1:478–84.
- [31] Makarouna M, Ullmann K, Lazarek K, Boening KW. Six-year clinical performance of lithium disilicate fixed partial dentures. *Int J Prosthodont* 2011;24:204–6.
- [32] Pelaez J, Cogolludo PG, Serrano B, Serrano JF, Suarez MJ. A four-year prospective clinical evaluation of zirconia and metal-ceramic posterior fixed dental prostheses. *Int J Prosthodont* 2012;25:451–8.
- [33] Kern M, Sasse M, Wolfart S. Ten-year outcome of three-unit fixed dental prostheses made from monolithic lithium disilicate ceramic. *J Am Dent Assoc* 2012;143:234–40.
- [34] Sola-Ruiz MF, Lagos-Flores E, Roman-Rodriguez JL, Highsmith Jdel R, Fons-Font A, Granell-Ruiz M. Survival rates of a lithium disilicate-based core ceramic for three-unit esthetic fixed partial dentures: a 10-year prospective study. *Int J Prosthodont* 2013;26:175–80.
- [35] Rinke S, Gersdorff N, Lange K, Roediger M. Prospective evaluation of zirconia posterior fixed partial dentures: 7-year clinical results. *Int J Prosthodont* 2013;26:164–71.
- [36] Sax C, Hammerle CH, Sailer I. 10-year clinical outcomes of fixed dental prostheses with zirconia frameworks. *Int J Comput Dent* 2011;14:183–202.
- [37] Marquardt P, Strub JR. Survival rates of IPS empress 2 all-ceramic crowns and fixed partial dentures: results of a 5-year prospective clinical study. *Quintessence Int* 2006;37:253–9.
- [38] Wolfart S, Bohlens F, Wegner SM, Kern M. A preliminary prospective evaluation of all-ceramic crown-retained and inlay-retained fixed partial dentures. *Int J Prosthodont* 2005;18:497–505.
- [39] Sulaiman F, Chai J, Jameson LM, Wozniak WT. A comparison of the marginal fit of In-Ceram, IPS Empress, and Procera crowns. *Int J Prosthodont* 1997;10:478–84.
- [40] Beschmidt SM, Strub JR. Evaluation of the marginal accuracy of different all-ceramic crown systems after simulation in the artificial mouth. *J Oral Rehabil* 1999;26:582–93.
- [41] Goldin EB, Boyd 3rd NW, Goldstein GR, Hittelman EL, Thompson VP. Marginal fit of leucite-glass pressable ceramic restorations and ceramic-pressed-to-metal restorations. *J Prosthet Dent* 2005;93:143–7.
- [42] Wettstein F, Sailer I, Roos M, Hammerle CH. Clinical study of the internal gaps of zirconia and metal frameworks for fixed partial dentures. *Eur J Oral Sci* 2008;116:272–9.